



**LUXFER'S SCBA CYLINDER  
VISUAL INSPECTION GUIDE  
VOLUME TWO:  
1988 - PRESENT**

**A Guide to the Visual Inspection of Luxfer SCBA Cylinders  
Manufactured in the USA between 1988 onwards**

Copyright (c) 1998 By Luxfer Inc. All rights reserved.  
Except as permitted under the U.S. Copyright Act of 1976,  
no part of this book may be reproduced in any form without  
the express written consent of Luxfer Inc.

Published in the USA by Luxfer Inc.

3016 Kansas Avenue  
Riverside, CA 92507  
USA  
Tel: (1) (909)-684-5110

First Edition, June 1998.

L SCBA G2 1998

## Table of Contents

Introduction .....	1
Visual Inspection Procedures .....	7
1. Frequency of Inspection .....	7
2. Before Inspection Begins .....	8
3. Preparing The Cylinder For Inspection....	11
4. Preparing The Exterior .....	14
5. Threads.....	18
6. Interior .....	20
7. Miscellaneous .....	22
8. Repairs to Composite Materials .....	23
9. Cylinder Condition - The Decision.....	24
10. Re-Installing Valves .....	26
11. Filling the SCBA Cylinder.....	27
Notes .....	29
Appendices .....	43
Appendix A.....	43
Appendix B .....	44
Appendix C .....	46
Appendix D.....	47
Appendix E .....	48
Appendix F.....	49
Glossary/Appendix G.....	51
Figures/Photos .....	61



# INTRODUCTION

Every day, emergency response team members (firefighters and hazmat team members) use self-contained breathing apparatus (SCBA) equipment in the performance of their job. It allows them to enter what otherwise is an unsafe environment to save lives and protect property.

SCBA equipment throughout the world is used several million times every year and has an excellent safety record. A major reason for that excellent record is the strict regulation of SCBA equipment in the USA and many other parts of the world.

The Luxfer SCBA cylinder is only one part of that complex respiratory equipment and the **care and maintenance of the Luxfer SCBA cylinder is the only focus of this Guide**. From this point on, usage of the term “SCBA” refers primarily to the Luxfer SCBA cylinder component.

It is also important to point out that this Guide is **not** meant to cover all visual inspections required or mandated by federal/state/local authorities or your SCBA manufacturer. This Guide covers **only** the technical, comprehensive external and internal inspections carried out by qualified technicians as part of government-mandated hydrotests or at times recommended by this Guide. Hereafter these technical inspections are referred to as “visual inspections.”

High-pressure SCBA cylinders are extremely tough and designed for the hard service they receive. Nevertheless, like all SCBA equipment components, cylinders must be treated with respect and be well maintained. Central to any prudent care and maintenance policy should be the visual inspection as recommended in this Guide and in all applicable rules and regulations.

This Guide is not intended to replace the need for professional training in how to carry out a professional visual inspection. In fact, Luxfer strongly recommends such training and the Guide includes a resource list of known training agencies. This Guide will, however, provide the trained inspector with the procedures and standards for visual inspections and additional resources a technician will need to carry out a thorough, professional visual inspection.

The professional staff at Luxfer who worked on developing this Guide want to acknowledge the considerable assistance received from many members of the SCBA community in making this Guide possible.

## NOTES:

- In developing these procedures and standards, Luxfer has complied with all known United States Department of Transportation (DOT) and other applicable governmental regulations and CGA standards applicable to all-metal and composite cylinders, both hoop-wrapped and full-wrapped, in the USA.
- In jurisdictions outside the USA, refer to your local regulations which may override any recommendations made in this Guide.
- **Remember, this Guide applies to the visual inspection of Luxfer-manufactured cylinders only.**

## HOW TO USE THIS GUIDE

This Guide provides you, the technician, with step-by-step instructions on how to carry out a visual inspection of all types of Luxfer SCBA cylinders manufactured in the USA from 1988 onwards. In 1988, Luxfer changed aluminum alloys and also began to manufacture full-wrapped cylinders. With all these changes, it made sense to publish two volumes of the Guide: **Volume One** covers cylinders made between 1972 - 1987, and **Volume Two** deals with cylinders manufactured from 1988 - present.

**Before you begin any inspection, you should make yourself familiar with the contents of this Guide.**

Included in the Guide are the following sections:

- 1. Categorizing Your Cylinder: Before you begin your inspection, you must determine what kind of cylinder you are about to inspect.
- 2. Frequency of Inspection: You must also decide how frequently you are going to inspect your SCBA cylinders. This will depend partly upon the type of cylinder and how it is used.
- 3. Before Inspection Begins: Everything you need to know to get ready for the inspection.
- 4-10. The Inspection Process: In seven sections, everything you need to know to take you through the inspection process.
- 11. Filling the SCBA Cylinder: Detailed instructions on how to properly and safely fill an SCBA cylinder.
- The NOTES: There is much information about the inspection procedures which, if included in the Inspection Process, would make it unwieldy and difficult to read. These NOTES are an important part of the inspection process and will help you understand some of the reasons **why** a particular instruction was given, or may elaborate on a particular point, or may explain how to do something. You **must** read and understand the NOTES before you conduct visual inspections on an SCBA cylinder. We recommend that you review the NOTES frequently.
- The APPENDICES: Useful lists and forms as well as sources for equipment, accessories and further technical references. Each APPENDIX should be reviewed as needed after its first reading. The Glossary of Terms is one of the Appendices.
- FIGURES and PHOTOS: To help you recognize things to look for during an inspection. Review them all before and while you are reading the Inspection Process sections.

## WARNINGS:

- Before using this Guide for the first time, read through and become familiar with all the sections, including the NOTES, APPENDICES, FIGURES and PHOTOS. If any part is unclear, contact Luxfer before inspecting the first cylinder. Remember, Luxfer recommends professional training for anyone visually inspecting cylinders.
- This Guide only applies to visual inspections of Luxfer high-pressure SCBA cylinders made from 1988 onwards. This Guide is not intended for the inspection of any other Luxfer cylinder; nor for inspecting SCBA cylinders, valves or other SCBA components equipment produced by another manufacturer. Contact the relevant manufacturer for their inspection materials.
- This Guide only applies to Luxfer high-pressure SCBA cylinders filled with air and used in a 'normal' environment (free of corrosive atmospheres and environments). For other applications or product usage, please contact Luxfer.
- To eliminate the risk of fire and serious injury, never fill a Luxfer SCBA cylinder with pure oxygen or oxygen-enriched air mixture or any other special gas. See NOTE 2 for additional information.

**NOTE: This Guide includes the inspection procedures for short-duration (5 and 10 minute) air cylinders used for emergency escape and limited reliance although not specifically referred to in the text.**

To contact Luxfer Gas Cylinders, see NOTE 7 for information.

## IMPORTANT

References to the NOTES, APPENDICES, FIGURES and PHOTOS in the following text are shown by the use of superscript numbers or letters and numbers, as follows:

NOTES: Superscript number alone, such as Luxfer Gas Cylinders<sup>7</sup> (i.e. NOTE 7)

APPENDICES: Superscript letter alone, such as The FORM<sup>G</sup> (i.e. APPENDIX G)

FIGURES: Superscript F with number, such as F<sup>4</sup> (i.e. FIGURE 4)

PHOTOS: Superscript P with number, such as P<sup>14</sup> (i.e. PHOTO 14)

## CATEGORIZING THE CYLINDER

Luxfer SCBA cylinders come in a variety of models, sizes and features. There are two basic categories: all-aluminum (also called all-metal) and composite. This Guide covers the care and maintenance of all-aluminum cylinders and both hoop-wrapped and full-wrapped composite cylinders.

### ALL-ALUMINUM

These SCBA cylinders are made of aluminum. The US Department of Transportation (DOT) regulates the visual inspection of aluminum cylinder surfaces (including the aluminum surfaces of composite cylinders). The applicable DOT regulations reference Compressed Gas Association (CGA) Pamphlet C-6.1 as the required procedure to follow.<sup>F</sup> Every SCBA cylinder inspector in the USA, or other countries following DOT regulations, must be familiar with and have the most current version of C-6.1.

### COMPOSITE

Composite cylinders consist of an all-aluminum inner cylinder or “liner” that is wrapped with resin-impregnated carbon, Kevlar, and/or glass fiber materials (see Glossary in APPENDIX G definitions, especially of **composite materials**). All composites have a resin component that holds in place all the fibers wrapped around the aluminum liner.

There are two basic categories of composite cylinders: **hoop-wrapped** and **full-wrapped** (also known as total wrapped).

**HOOP-WRAPPED CYLINDERS:** These are a combination of exposed aluminum surfaces and composite materials where the composite material is only on the cylindrical portion.

**FULL-WRAPPED CYLINDERS:** These have composite material wrapped all over the aluminum metal liner. The only non-composite material visible on the outside of the full-wrapped cylinder is in the neck region (see FIGURE 6), where the valve connects.

The DOT regulates the visual inspection of composite surfaces. The applicable DOT regulations reference CGA Pamphlet C-6.2 as the required procedure (see APPENDIX F). Every SCBA cylinder inspector in the USA, or in other countries conforming to DOT regulations, must be familiar with and have the most current version of C-6.2 at hand.

To be able to inspect the composite materials on your cylinder, you will also need to identify the cylinder category. All composite cylinders, whether hoop-wrapped or full-wrapped, fall into one of four categories: **GROUPS A, B, C or D**.

To identify your cylinder category, look on its label for its Part Number or Prefix code. (For examples, see FIGURES 3 and 4.) Then, look at the chart. Find the group containing your cylinder identification and, where relevant in the inspection process, follow the procedures for that group.

GROUP A		GROUP B		GROUP C		GROUP D	
PART NUMBER	PREFIX NUMBER	PART NUMBER	PREFIX NUMBER	PART NUMBER	PREFIX NUMBER	PART NUMBER	PREFIX NUMBER
L08W	RD	L45T	TB	L87T	CI	L45E	IH
L13W	WG	L45H	OW	L87H	OU	L45G	IJ
L15W	TL	L45W	WF			L45J	IO
L17W	WH	L60K	OT			L45M	OK
L17A	WO	L66T	TD			L45S	OJ
L18W	TH					L62M	OL
L23W	WZ					L65G	IL
L24W	WY					L65M	OM
L45N	WK					L87G	OP
L45B	TF					L87M	ON
L45I	OV						
L45F	TA						
L62W	WS						

**NOTE: Remember, these procedures are for the composite materials on your cylinder. You must follow the aluminum inspection procedures for any and all aluminum portions of every composite cylinder.**

For your general guidance:

- **Group A** cylinders include hoop-wrapped and full-wrapped cylinders. You will follow Group A inspection limits for the composite portion of the cylinder.
- **Group B** cylinders include hoop-wrapped and full-wrapped cylinders. You will follow Group B inspection limits for the composite portion of the cylinder.
- **Group C** cylinders are full-wrapped cylinders. You will follow Group C inspection limits for the composite portion of the cylinder.
- **Group D** cylinders are only carbon full-wrapped cylinders. You will follow Group D inspection limits for the composite portion of the cylinder.

It is also important to know that physical damage (abrasion, dents, digs, scratches, cuts, gouges, etc.) to composite surfaces is categorized into three levels in CGA C-6.2. There is **Level 1**, **Level 2** and **Level 3** damage.

- **Level 3** damage requires the condemnation of the cylinder.
- **Level 2** damage may be repaired and the cylinder must then be hydrotested prior to returning to service. If the owner of a composite container with Level 2 damage chooses not to have the container repaired (or the regulatory authority doesn't allow the cylinder to be repaired), the cylinder must be condemned.
- **Level 1** damage is usually noted in the cylinder record/log or owner form<sup>p</sup> and the cylinder is acceptable to return to service (providing it passes the rest of the visual inspection and its regular hydrotest).

Remember, this damage categorization refers only to the composite portion of the SCBA and refers to the physical conditions of the composite materials.

**NOTE: Remember, these procedures are for the composite materials on your cylinder. You must follow the aluminum inspection procedures for any and all aluminum portions of every composite cylinder.**

Before you begin any inspection, you will also need to know the cylinder's thread type in order to determine if there are enough threads to meet thread requirements.



This page is intentionally left blank.



# INSPECTION

## 1 FREQUENCY OF INSPECTION

Every SCBA cylinder that has been well cared<sup>4</sup> for and is in good condition should be thoroughly inspected visually, both internally and externally, at the time of its hydrostatic retesting<sup>1</sup> or at any opportune time before that point.

In certain circumstances, **immediate** visual inspection of an SCBA cylinder is strongly recommended. These circumstances are defined as including when the cylinder:

1. Has obviously not been well cared<sup>4</sup> for and maintained;<sup>4</sup>
2. Dropped, fell, was struck, or was in an accident;
3. Was stored improperly<sup>4</sup> or shows signs of damage;
4. Has obvious corrosion since the last visual inspection, or has been exposed to chemicals or an extremely corrosive atmosphere/environment;
5. Has a gouge, dent, scrape, cut, dig, loose fibers, missing resin or in any way has been damaged (including severe abrasion) since the last visual inspection;
6. Was stored with water, material or matter inside the cylinder, or was stored in a place where it was in chemicals or corrosive materials;
7. Shows signs of exposure to fire or high heat,<sup>20</sup> including any one or more of the following:
  - Charring<sup>p27</sup> or blistering of the resin, paint or protective coating;
  - Melting or charring of the metal;
  - Distortion of the cylinder and/or any cylinder accessory;
  - Removal of any resin that loose fibers are visible
  - Resin has a brown discoloration
  - Melting of fuse plugs, valve handwheel, valve protector, and/or any other valve component or cylinder accessory;
8. Has been partially or fully repainted or treated to hide suspected damage and/or fire damage;
9. Is known or suspected to be leaking;
10. Is known or suspected of having a crack; or,
11. Was found empty (when it should have been full) and there is no known reason for it to be empty.

**WARNING:** If a cylinder is known to have been subjected to any unusual treatment, accident, or condition, it should be immediately taken out of service, depressurized and visually inspected before it is returned to service or, if necessary, condemned.

## 2 BEFORE INSPECTION BEGINS

If there is any part of the following procedure that is unclear, please contact Luxfer<sup>7</sup> for assistance.

A work station should be made ready to do visual inspections. Select an area and table which will not cause damage to the cylinder or equipment. The table should be flat, level, and padded (e.g., old carpet, carpet remnants, rugs, etc.). Lighting in the area should be bright. The table should be equipped with a holder or blocks to keep a cylinder on its side from rolling, without damaging the cylinder or valving.

The inspector should be alert, clear-headed and observant. The visual inspection depends upon the knowledge, experience and senses of the inspector.

Luxfer recommends that all inspectors responsible for visual inspections are trained and accredited as visual cylinder inspectors. For a listing of inspection training agencies, see APPENDIX A.

The inspection equipment and accessories should be gathered together. A list of accessories can be found in APPENDIX B and a list of sources in APPENDIX C. All equipment and accessory items should be inspected before use for defects or damage, and all should be made fully operational.

Obtain a SCBA CYLINDER VISUAL INSPECTION FORM (otherwise referred to as THE FORM) for each cylinder to be inspected, or use the sample in APPENDIX D.

A log may be used and kept by an inspector instead of using THE FORM, especially when the cylinders are all owned by the inspecting group (e.g., the inspectors doing the inspecting are employees of a fire station which owns and maintains the cylinders).

If the inspector is inspecting a third-party SCBA cylinder, an OWNER'S RELEASE FORM should be completed prior to the inspection. An example of an Owner's Release Form can be found in APPENDIX E.

Complete the cylinder ownership information on THE FORM, prior to the inspection. Leave no place blank on THE FORM and be descriptive in the fill-ins.

A completed copy of THE FORM is to be kept by the inspector/organization, and a copy provided to the owner (if the owner is not the organization conducting the inspection).

The inspection procedures that follow contain detailed instructions on what to do as you proceed through the inspection. These instructions include the following actions:

**RECORD, DO NOT RETURN TO SERVICE, REPAIR, CONDEMN, CONTACT and RETURN TO SERVICE.**

**RECORD:** As you carry out the inspection, make detailed notes (of your observations) on THE FORM.

**DO NOT RETURN TO SERVICE:** The cylinder cannot return to service until some action has been taken to correct an unacceptable situation.

**REPAIR:** Applies to composite cylinders only. Under certain conditions, the composite portion of the composite SCBA may be repaired. Follow the instructions on how to carry out repairs. After the repair is complete, the cylinder must be hydrostatically tested before being put back into service.

**CONDEMN:** If a condemnable feature is found, the inspection stops at that point and the cylinder is rendered unfit for further use.

**ACCEPT WITH NOTATION:** The inspection procedure sometimes uncovers cylinder conditions which do not warrant condemning the cylinder but which do require that it is inspected more frequently than a cylinder which can otherwise return to service (see next definition below). Owners should be advised of the condition and on how they can prevent further occurrence of this condition.

**CONTACT:** There may be circumstances where it is advisable to contact the manufacturer's representative for more information before proceeding further. To contact Luxfer, see NOTE 7.

**RETURN TO SERVICE:** The cylinder has passed its visual inspection and may go back into service. You may or may not, depending upon industry usage, affix a label to the cylinder indicating when and by whom it was inspected. At no time may a visual inspector put any markings<sup>6</sup> on a cylinder nor embed label(s)<sup>6</sup> with resin to the composite portion of a container to be returned to service.

See GLOSSARY for complete definitions of **condemn** and **repair** and **acceptable with notation**.

Before beginning the inspection, remove all SCBA accessories from the cylinder (i.e., backplate, harness, cover, boot, bands, straps, etc.). Only the cylinder itself is needed for this inspection. If the cylinder is valved, the inspector should remove it prior to inspection, as suggested below. Contact the SCBA or respirator manufacturer for the proper inspection procedure of the valve.

The cylinder must be empty of pressurized air for inspection. Slowly discharge the pressurized air from the valved cylinder according to recommendations by the SCBA or respirator manufacturer. Record if any leak was detected (see section 5 A.). We recommend that it take over 10 minutes to discharge a full cylinder, to qualify as a 'slow discharge.'

When the cylinder is empty, remove the valve. The valve should be removed according to the SCBA or respirator manufacturer's recommendations so that the valve and cylinder are not damaged.

***CAUTION: If the valve is damaged or not functioning properly, the inspector/operator may think that the cylinder is empty after opening the valve and not hearing any gas released. All valved cylinders thought to be empty should still be handled as if they are under pressure, and the valve should be removed carefully, according to the respirator manufacturer's guidelines.***

If, for any reason, the valve is hard to remove, stop.

Check to see that the valve is functioning properly by adding a small amount of air to the cylinder to prove that air goes in and out of the valve. Depressurize and then proceed to remove the hard-to-remove valve, only after this valve check shows that the valve is working properly and that the cylinder has been depressurized. For further instructions, contact the respirator manufacturer if the valve isn't working according to the SCBA manufacturer.

We recommend the inspection of the valve at this time. Contact the respirator manufacturer for the proper inspection procedure of the valve.

## 3 PREPARING THE CYLINDER FOR INSPECTION

The visual inspection begins by:

- recording cylinder markings
- making general observations
- preparing the cylinder interior for inspection by removing any internal contaminants (water, materials, debris or contents), and finally
- preparing the cylinder exterior for inspection.

### 3A CYLINDER MARKINGS

Remove any loose paint or anything obstructing the reading of the stamped cylinder information located on the crown of the all-metal and hoop-wrapped SCBA cylinder. See FIGURES 1 and 2 for illustrations and NOTE 16. Do not attempt to remove resin, paint, or fibers on the composite portion of the cylinder.

If Luxfer's original cylinder manufacturing label<sup>6</sup> information is obscured on hoop or full-wrapped cylinders, please read below.

RECORD all relevant cylinder information from the cylinder on the SCBA CYLINDER VISUAL INSPECTION FORM or Cylinder Log<sup>p</sup> (Referred to as "THE FORM" below).

RECORD marking<sup>6</sup> and label<sup>6</sup> information you see, including: Government specification, service pressure, serial number, and hydrostatic test dates: original, all previous, and latest hydrostatic test date. See FIGURES 1 through 4 for examples.

The first FIGURES, 1 and 2, depict examples of cylinder marking layout. A list of "Markings" under each diagram shows the possible marking variations for each layout. In other words, look at each FIGURE as an example of marking design. Then read the list of Markings<sup>6</sup> below the diagram to learn what different markings could be in that design.

FIGURES 3 and 4 depict how original labels<sup>6</sup> appear embedded at time of manufacture in the composite material.

Original label<sup>6</sup> damage or illegibility can be cause for condemning a cylinder. If the serial number is no longer legible, the cylinder must be condemned or Luxfer<sup>7</sup> contacted for advice. An SCBA cylinder that is known to be a Luxfer cylinder, which still has a legible serial number, can be returned to service only after all the other product information is made legible. For instance, an illegible part of a composite SCBA cylinder label which has the part identification on it can be corrected by putting that information back on the cylinder, only if the serial number is still legible on the label. Note that some Luxfer full-wrap SCBA cylinders have the serial number stamped on the neck in addition to the serial number marking on the manufacturer's cylinder label. Contact Luxfer<sup>7</sup> for further advice, if needed.

RECORD the Category of the composite cylinder (according to **CATEGORIZING THE CYLINDER** guidelines above). Also, RECORD the thread type on THE FORM.

RECORD if the cylinder was under pressure prior to the inspection, or empty.

**WARNING:** Luxfer SCBA cylinder marking does not include the plus sign (+). If a plus sign is found on a Luxfer SCBA cylinder (stamped into the metal), contact Luxfer<sup>7</sup> and do not return that cylinder to service.

RECORD if you are aware that the cylinder was repaired previously.

CONDEMN all cylinders with altered or unreadable serial numbers.<sup>F1-4</sup>

CONTACT LUXFER<sup>7</sup> if cylinder manufacturer labels or markings are illegible or missing identification or other information.

DO NOT RETURN TO SERVICE any cylinder that has not been hydrostatically tested within its required time.<sup>1</sup>

DO NOT RETURN TO SERVICE any composite cylinder that has been repaired, without first hydrostatically testing it.

## 3B GENERAL OBSERVATIONS

RECORD what you know or can see about the cylinder condition (signs of wear), maintenance, exposure to unusual treatment or conditions, evidence or knowledge of exposure to heavy service or extreme/hazardous service, (see Section 1 above and Glossary<sup>G</sup> for definitions of the types of service).

RECORD if there is evidence<sup>P27</sup> or knowledge of cylinder exposure to heat and/or fire. See Section 1D above for more information about unusual treatment, accident or condition.

RECORD if fresh paint is found. If fresh paint is found, get information about how *and* why it was painted and how the paint was cured and dried. RECORD this information on THE FORM, as well.

RECORD if there is evidence or knowledge that the cylinder had previously been repaired.

RECORD any information about the care<sup>4</sup> the cylinder has received.

CONDEMN all **unattended** cylinders left exposed or suspected of having been exposed to temperatures in excess of 350°F (175°C) or **unattended** cylinders that have been exposed to the direct action of fire. Special circumstances apply when the SCBA cylinder is being worn and used by a firefighter exposed to excessive temperatures. **Read NOTE 20 which explains the reasons for this exception.**

CONDEMN all cylinders which exhibit any arc or torch burns,<sup>P13</sup> or fire damage.<sup>P27</sup>

CONDEMN all cylinders that were repainted and heated over 350°F (175°C) to dry or cure the paint.

CONDEMN all composite cylinders if there is any noticeable lifting or peeling of the composite materials.<sup>P25</sup>

CONDEMN all cylinders which may have been crushed (exhibit a non-round shape).

DO NOT RETURN TO SERVICE all cylinders with fresh paint until it passes a hydrostatic retest, unless the inspector is sure the fresh paint doesn't hide an imperfection.<sup>G</sup> Fresh paint may also hide heat damage.

**WARNING: Do not return to service any cylinder with hidden heat or physical damage that cannot be visually inspected.**

## 3C PREPARING THE INTERIOR

Pour out any contaminating material from the interior into a sufficiently strong and large bowl or container.

RECORD on THE FORM any unusual odors.

Inspect any and all material or matter that was poured from the cylinder. Identify and/or describe this material<sup>11</sup> on THE FORM. If at this time the cylinder has material 'stuck' in it, invert the cylinder over a white piece of paper, holding it about one half inch (1/2 inch) above the paper. Then allow the cylinder to drop onto the paper, releasing any of the remaining contents of the cylinder onto the paper.

Bag all these materials in a plastic bag or seal in a jar, to show the owner. RECORD observations<sup>11</sup> on THE FORM. RECORD the kind and source of contents.

DO NOT RETURN TO SERVICE any cylinder with gummy internal substances, oil and/or debris, or which have an offensive odor. Hold for internal cleaning.<sup>17</sup>

DO NOT RETURN TO SERVICE any cylinder with an internal contaminate. After cleaning,<sup>17</sup> the cylinder may then be reinspected (starting at the beginning of this procedure).

**NOTE: Train and educate all owners on the proper filling, care and maintenance of SCBA cylinders<sup>4</sup> if water, debris, lubricants, oils, etc. are found inside the cylinder. Ask them to adhere to the recommendations.**



## 4 PREPARING THE EXTERIOR

The entire exterior of the cylinder must be exposed to the inspector and not concealed. Do not remove paint unless it is lifting off.<sup>16</sup> If decals and/or stickers hide damage or suspected damage, then they should be removed. Signs of damage or suspected damage include, but are *by no means* limited to, scraped labels, evidence of impact, bubbling up or distortion of labels. Contact those who put on the decals or stickers for removal procedures<sup>18</sup> and authorization. If the source of the sticker or decal is unknown, lift off enough of the label to inspect the cylinder surface below. Use only removal procedures which do not harm aluminum or composite materials. (Make sure to replace any cautionary stickers or labels after the inspection). Do not remove or attempt to remove any labels imbedded in the resin.

- There should be no cylinder equipment attached during the inspection process.
- There should be no external material or condition which prevents a visual inspection of the surface.
- If there are external contaminants, refer to NOTE 16 for proper cleaning of the exterior.

### 4A BULGES, BOW AND DENTS

#### Aluminum Cylinders

Check for bulges, bows (“banana”) and dents. Roll cylinder on padded table to find bulges and bows; hold a straight edge against its sidewall in several places and the base, to find dents and more bulges or bows. Check crown for dents. See PHOTOS 1 and 18 and FIGURES 10 and 11.

Determine the dent depth and diameter using a straight edge and ruler. RECORD this information and the location of the dent on THE FORM. Read NOTE 6.

Look for a bow and bulges: If a straight edge rises from the cylinder sidewall and light is clearly visible between the edge and cylinder surface, then a bulge or bow is indicated. Further determine if the condition is a bow or bulge.

If the shape of the cylinder is a curve<sup>P18</sup> then RECORD on THE FORM that the cylinder is bowed.

If the rise is in a distinct area and is definitely visible (light is clearly seen between the straight edge and the cylinder; the straight edge wobbles on bulge,<sup>F10</sup> record on THE FORM as a bulge. RECORD the bulge's location on THE FORM.<sup>6</sup>

- CONDEMN cylinders with dents 0.060 inch (1.53 mm) or greater in depth in the aluminum.
- CONDEMN cylinders with dents measuring less than two inches in diameter in the aluminum.
- CONDEMN cylinders with definite visible bulges in the aluminum.
- ACCEPT cylinders with bows.
- ACCEPT WITH NOTATION cylinders with dents near but under 0.060 inch (1.53 mm) in depth in the aluminum.
- RETURN TO SERVICE aluminum bowed cylinders. If unsure whether it is a bow or bulge, refer to FIGURES 10 and 11 and PHOTO 18. Contact Luxfer if you are still unsure.<sup>7</sup>

## Composite Cylinders

Check for bows, bulges and dents as is outlined above in the aluminum section. A composite material dent may appear as a frosty area rather than an indentation. Measure and determine the area of any noted frosty area(s).

- CONDEMN cylinders with dents in the composite material which cause the breaking or loosening of fibers, or when structural damage is apparent.
- CONDEMN cylinders with dents in the composite material which causes a 'frosty' appearance that is 1.0 square inch (6.45 cm<sup>2</sup>) or more in area.
- CONDEMN composite cylinders with bows and/or bulges.

## 4B CUTS, GOUGES, SCRATCHES, ABRASION

Check for cuts, digs, gouges and scratches both in the metal and in the composite material. See APPENDIX G for definitions, including the definition of **transverse**.<sup>6</sup> See PHOTOS 2, 3, 21, 22, 23, 24, 25, and 26. The current CGA pamphlet C-6.2 defines levels of types of damage to composite cylinders as: Level 1 (return to service), Level 2 (repairable damage), and Level 3 (condemn cylinder). The current CGA pamphlet C-6.1 defines inspection criteria for aluminum cylinders.

### Aluminum Cylinders

Gently and carefully, with a file, smooth any upset metal (metal raised up from the cylinder surface from the cut, dig, gouge, or scratch) without causing damage to the cylinder or composite material. This is in order to get a true depth measurement of the cut, dig, gouge or scratch in the metal.

Measure the length, depth<sup>p28</sup> and location of all cylinder surface cuts, digs, gouges or scratches. Note whether the cuts, digs, gouges or scratches in the composite material are transverse<sup>6</sup> to the fiber direction.<sup>p23</sup> Read NOTE 6. RECORD information and location(s) on THE FORM.

- CONDEMN all cylinders with surface cuts, digs or gouges in the metal that are either longer than six inches, or deeper than 0.030 (thirty thousandths) inch (0.76 mm).

### Composite Cylinders

RECORD on THE FORM all information, findings, measurements and location(s) of any damage.

- CONDEMN composite cylinders with cuts, digs, scratches, abrasion<sup>6</sup> or gouges in the composite material (transverse to the fiber direction) deeper than the depths given in Table 1 and of any length (for the category of cylinder you are inspecting). See PHOTO 26. Level 3 damage.
- CONDEMN composite cylinders with cuts, digs, scratches, abrasion or gouges in the composite material in any direction which occurs in previously repaired (see SECTION 8) areas. Level 3 damage.
- CONDEMN composite cylinders if the repaired area resin shows signs of poor adhesion or is 'lifting off' the composite surface.

- CONDEMN composite cylinders with cuts, digs, scratches, abrasion or gouges in the composite material which are transverse and longer than one inch (25.4 mm) in length and more than 0.005 inches (0.13 mm) deep. Level 3 damage.
- CONDEMN composite cylinder with abrasion damage of any depth which loosens or breaks fiber(s) in the wrapping.<sup>P25</sup>
- REPAIR composite cylinders with cuts, digs, scratches, abrasion or gouges in the composite material greater than 0.005 inches (0.13 mm) in depth, less than the depths given in TABLE 1 and shorter than one inch (25.4 mm) long (for the category of cylinder you are inspecting). Level 2 damage. Hydrostatic test cylinders after the repair and reinspect before filling.

<b>TABLE 1.</b>	<b>Transverse</b>	<b>Composite Damage</b>
Cylinder Category GROUP	Maximum Allowable Depth of Damage on Cylindrical Portion	Maximum Allowable Depth of Damage on Dome/Base Portion
A	0.02 inches (0.51 mm)	0.01 inches (0.25 mm)
B	0.04 inches (1.02 mm)	0.02 inches (0.51 mm)
C	0.06 inches (1.52 mm)	0.03 inches (0.76 mm)
D	0.035 inches (0.89mm)	0.03 inches (0.76 mm)

- Determine the Cylinder Category from the chart in **CATEGORIZING THE CYLINDER**.

***No composite material may be repaired if the imperfection is longer than one inch (25.4 mm).***

Transverse damage with depths greater than those listed in TABLE 1 is Level 3 damage. Transverse damage with depths greater than 0.005 inches (0.13 mm) and less than the depths listed in TABLE 1 and shorter than one inch (25.4 mm) long, is Level 2 damage (repairable). All damage less than 0.005 inches (0.13 mm) deep is Level 1 damage.

Abrasion damage under one square inch (645 mm<sup>2</sup>) in area (in any direction) may be repaired if it is deeper than 0.005 inches (0.13 mm), but less than the depth listed in TABLE 1. See PHOTO 26. If it is less than 0.005 inches deep, it doesn't need repair and may be returned to service. If the abrasion covers an area great than one square inch and is deeper than 0.005 inches, the cylinder must be condemned.

All repaired cylinders must be hydrotested and reinspected prior to filling and use.

## 4C EXTERNAL SURFACE CORROSION

### Aluminum Cylinders

Check external metal surfaces for corrosion. Determine the type of corrosion and the depth of what seems to be the deepest pit or deepest part of the broadspread corrosion. See NOTES 5 and 6.

Record the location and whether the corrosion is an isolated pit corrosion, line or broadspread corrosion on THE FORM. (For visual examples, see FIGURES 9 and PHOTOS 11 and 12.)

- CONDEMN all cylinders with one or more external corrosion pits over 0.060 inch (1.53 mm) deep in the sidewall, crown and/or base.
- CONDEMN all cylinders with external line or broadspread corrosion when one or more pit, or the broadspread corrosion is over 0.030 inch (0.76 mm) deep in the sidewall or crown.
- CONDEMN all cylinders with external line corrosion over six inches (152 mm) long.
- CONDEMN all cylinders with broadspread corrosion covering more than 25 percent of the area.
- If other pits are present, check a few more pit depths to be sure the cylinder is fit to return to service.

### Composite Cylinders

Composite materials can be attacked by chemicals<sup>19</sup> and, in some cases, by treated water. The external composite surfaces must be checked for any visible signs of such chemical exposure.

- CONDEMN composite cylinders with unknown chemical residues on or in the composite material.
- CONDEMN composite cylinders known to have been covered, splashed or left standing (soaked) in unknown chemical(s) such that the composite material came in contact with the chemical(s).
- CONDEMN composite cylinders if the composite portion is discolored, blotchy or the paint and/or resin shows signs of chemical attack (e.g., paint or resin has softened, smeared, bubbled, etc.).
- CONDEMN composite cylinders if the composite portion has come into contact with a type of chemical that deteriorates or may deteriorate the composite material.<sup>19</sup>
- HOLD composite cylinders if the composite portion has come into contact with a type of chemical that isn't listed<sup>19</sup> and if you are unsure of its effects on the composite material. Contact Luxfer<sup>7</sup> for advice.

## 5 THREADS

- Thread imperfections include metal loss, galling, corrosion, cracking and abuse.
- Abuse can appear as deep nicks, broken threads, cross threads,<sup>6</sup> stripped threads, and threads without well defined and sharp peaks.
- Careful inspection of threads is critical to the proper operation and safety of the Luxfer SCBA cylinder.
- Be familiar with what is known as a tool stop mark. See NOTE 14, PHOTO 10, and see the Glossary<sup>6</sup> for definitions of the various kinds of thread imperfections.
- Clean threads of any debris and lubricant<sup>9</sup> before proceeding.

**WARNING: DOT E 7235 SCBA cylinders marked with a 4500 psig service pressure must be equipped with a steel neck ring. If the steel neck ring is not present, immediately withdraw from service and contact Luxfer.<sup>7</sup>**

### 5A LEAKS

From information gathered while releasing any pressurized air, or from prior knowledge, or from discovering an empty SCBA cylinder (that should have been full or partially full), RECORD if you are aware that the cylinder has been leaking.

Determine the cause of the leak<sup>6</sup> (e.g., valve, O-ring, cylinder threads, cylinder, etc.).

CONDEMN all cylinders where the leak at the valve connection is caused by a damaged cylinder, defective threads, or imperfections in the neck area.

**WARNING: Immediately withdraw from service any DOT E 7235 SCBA cylinder marked with a 4500 psig service pressure that does not have a neck ring. Contact Luxfer.<sup>7</sup>**

### 5B THREAD IMPERFECTIONS

Inspect clean cylinder threads with and without a dental mirror and light. See NOTE 8 and PHOTOS 4 - 9. Inspect cylinder threads for any imperfections.<sup>6</sup> Check for corrosion on cylinder thread as well as valve thread, if valve is available.

RECORD on the form the location of all thread imperfections (damaged, missing, and cross threads).

Count the number of continuous full threads, starting at the top, that do not have imperfections. RECORD this number of good threads on THE FORM.

Cylinders must have a specified minimum number of continuous full threads as required in applicable thread standards. The overriding requirement is a minimum number of threads so that a gas-tight seal can be obtained by reasonable valving methods.

Know the cylinder's (recorded) service pressure and then review Table 2. If you cannot determine the thread type, contact Luxfer<sup>7</sup> for advice. Each Luxfer cylinder part number has a specific thread type, and a Luxfer representative can provide you with this information.

CONDEMN all cylinders that do not have the required minimum number of continuous full threads without imperfection, counting from the top according to TABLE 2 criteria.

<b>TABLE 2. Thread Requirements</b>			
<b>Thread Type</b>	<b>Service Pressure (psig)</b>		
	2216	3000	4500
	<b>Minimum Required Threads</b>		
0.750-16UNF-2B	6	7	10
0.750-14NSPM-2B	6	8	12
0.875-14UNF-2B	6	7	10
1.125-12UNF-2B	6	8	12

CONDEMN all cylinders with corrosion in a thread that is a continuous full thread required and defined above.

## **5C CRACKED CYLINDER THREADS**

Inspect all cylinder threads for cracking with and without a dental mirror and light. See PHOTOS 6 - 9. In addition to a visual inspection using the naked eye, the use of an Non-destructive Testing (NDT)<sup>G</sup> device, such as Visual Plus<sup>B&C</sup> is also recommended to detect thread cracks.

Remove the O-ring. Inspect the O-ring gland and cylinder face<sup>F5/6</sup> for cracking. Follow the SCBA or respirator manufacturer's recommendation on when to replace the O-ring.

**NOTE: SCBA components, like the O-ring, are certified by regulatory agencies in the USA. DO NOT replace components without following the SCBA manufacturer's instructions. Replace components with parts that are authorized by the SCBA manufacturer.**

CONDEMN all cylinders that show evidence of cracking in more than one continuous full thread.<sup>G</sup> Contact Luxfer<sup>7</sup> with this information and findings.

CONDEMN all cylinders with O-ring gland or face cracks. Contact Luxfer<sup>7</sup> with this information and findings.

CONDEMN all cylinders with O-ring gland or face damage.

RETURN TO SERVICE all cylinders with tool stop marks <sup>P10</sup> on otherwise acceptable threads, with acceptable glands and faces.

## **5D FOLDS AND VALLEYS IN THREADS**

Inspect cylinder threads near the bottom (closest to the inside of the cylinder) of the threaded area, with a dental mirror and light<sup>8</sup> for folds and valleys that enter into the thread area. For visual illustrations, see FIGURES 6 - 8 and PHOTOS 14 - 17.

RECORD the findings on THE FORM.

CONDEMN all cylinders with valleys that reduce the number of defect-free, continuous full threads below the minimum (according to the limits defined in section 5B.), counting from the top. Contact Luxfer<sup>7</sup> with this information and findings.

CONDEMN all cylinders with a fold which enters into more than one thread. Contact Luxfer<sup>7</sup> with this information and findings.

## 6 INTERIOR

Nothing must obscure the interior metal surface of the cylinder from visual inspection.

If the interior metal surface cannot be seen after removing loose contents and water (because of such things as stains, deposits, heavy corrosion, material still clinging to the inside, etc.), arrange to have the cylinder cleaned. See NOTE 17.

Proceed only if the interior surface is readily visible.

See NOTE 12 for further information on standard interior surface appearances in Luxfer SCBA cylinders.

### 6A INTERIOR THREAD AREA

Inspect all cylinders with a dental mirror and light, just below the threads and inside the cylinder crown area for any sign of cracks, folds and valleys. See NOTE 10. (See PHOTOS 14 - 17 and 20 and FIGURES 6 - 8).

Determine the location of any crack, fold, and valley. Measure the depth of any and all folds.

RECORD all information on THE FORM.

CONDEMN all cylinders that show evidence of cracking.<sup>p20</sup> Contact Luxfer<sup>7</sup> with this information and findings.

CONDEMN all cylinders with one or more folds in the interior crown area deeper than 0.060 inches (1.53 mm). Contact Luxfer<sup>7</sup> with this information and findings.

RETURN TO SERVICE all cylinders with interior valleys in the crown area.<sup>10</sup>

### 6B METAL IRREGULARITIES

Inspect cylinder interior with a light for any metal irregularities. Cylinders may show interior irregularities that may have been caused by exterior impacts. These include, but are not limited to, indentations or liner distortions (in composite cylinders).

RECORD the location and observations of all such irregularities on THE FORM.

Contact Luxfer<sup>7</sup> with any observations you question.

CONDEMN all cylinders that show any cracks in the interior sidewall, base, and/or crown. Contact Luxfer<sup>7</sup> with this information and findings.

CONDEMN aluminum cylinders that show any interior sidewall or base metal distortions. Contact Luxfer<sup>7</sup> with this information and findings.

CONDEMN composite cylinders that show interior liner indentations or distortions.

## 6C INTERIOR CORROSION AND PITTING

The concern of corrosion is that it has the potential of reducing cylinder material, as has been previously mentioned and covered in the Glossary: see **material loss**.

Before proceeding, the inspector must be sure which type of cylinder interior is being inspected, and then apply only the appropriate criteria for that design.

Inspect interior sidewall, crown and base with a light for any corrosion or pitting.

Determine the type, depth, location and length (for line corrosion) of the corrosion. See NOTES 5 and 6. For visual illustrations, see PHOTOS 11 and 12. RECORD location, type and depth of corrosion on THE FORM.

### **Aluminum Cylinders**

CONDEMN all cylinders with any interior isolated corrosion pit estimated to be over 0.060 inch (1.53 mm) deep.

CONDEMN all cylinders with interior sidewall line or broadspread corrosion when one or more interior pits in the line corrosion is deeper than 0.030 inch (0.76 mm), and/or if the interior broadspread corrosion is deeper than 0.030 inch (0.76 mm).

### **Composite/Hoop-Wrapped Cylinders**

CONDEMN all hoop-wrapped cylinders with internal isolated corrosion pit(s) estimated to be over 0.060 inches (1.53 mm) deep.

CONDEMN all hoop-wrapped cylinders with sidewall line or broadspread corrosion when one or more interior pit in the line corrosion is deeper than 0.030 inch (0.76 mm), and/or if the interior broadspread corrosion is deeper than 0.030 inch (0.76 mm)

### **Composite/Full-Wrapped Cylinders**

CONDEMN all full-wrapped cylinders with internal isolated corrosion pit(s) estimated to be over 0.03 inches (0.76 mm) deep.

CONDEMN all full-wrapped cylinders with sidewall line or broadspread corrosion when one or more interior pit in the line corrosion is deeper than 0.020 inch (0.51 mm), and/or if the interior broadspread corrosion is deeper than 0.020 inch (0.51 mm)

### **Aluminum and Composite**

CONDEMN all cylinders with interior sidewall line corrosion that is over 6 inches (152 mm) long (any depth).

CONDEMN all cylinders with an interior surface that looks like it was blasted, ground, sanded, cut or has lost metal.

HOLD the cylinder for internal cleaning<sup>17</sup> if corrosion obstructs a clear view of the interior's surface.

If other pits and/or corrosion are found, check them to determine if the cylinder is fit to return to service.

Train and educate the owner on the proper care and maintenance of the cylinder if any corrosion is found. See NOTE 4.



## 7 MISCELLANEOUS

This procedure does not cover valve inspection or the inspection of any SCBA component other than the SCBA cylinder. Check with the manufacturer of the SCBA for the proper handling and inspection of the other components.

Especially check with the SCBA manufacturer on the inspection of any valve component (rupture discs or pressure relief device, dip tube, valve threads, O-rings, etc.) and the condition which requires their replacement.

***CAUTION: SCBA components [like the valve and O-ring] are certified by regulatory agencies in the USA. DO NOT replace components without following the SCBA manufacturer's instructions. Replace components with parts that are authorized by the SCBA manufacturer.***

If the valve or valve component did not pass inspection, or if the valve was not inspected at all, do not attach the valve to the cylinder. Instead, return each separately to the owner, explaining the concern or problem or relaying that the valve was not inspected.

The end of THE FORM is set aside to describe these and other concerns or problems with accessories or the cylinder that were not covered above. RECORD specific and clear comments.

## 8 REPAIRS TO COMPOSITE MATERIALS

Under certain circumstances, composite cylinders may be repaired. The portion permitted for repair is only the composite material itself (not metal portions, threads, liners, or other places on the cylinder). Repair can only be done on the composite area of the cylinder when the damage is qualified for repair (Level 2 damage) through the above inspection criteria. These repairs are minor in nature and are meant to help extend the safe life of the cylinder.

The suitable conditions, procedures and directions for making a repair to the composite material are given in NOTE 13.

**WARNING: All level 2 damage repaired composite cylinders must be hydrotested and visually reinspected before being returned to service.**

## 9 CYLINDER CONDITION - THE DECISION

- A. If there are no recorded conditions sufficient to condemn the cylinder, then RECORD on THE FORM the cylinder status as ACCEPTABLE. Proceed to section 9E.
- B. If the composite portion of a composite cylinder has one or more repairable conditions (Level 2 damage) then have the cylinder repaired.<sup>13</sup> Have the cylinder hydrotested prior to returning the cylinder to the owner, and/or prior to filling the cylinder. If it passes hydrotest, visually reinspect the cylinder. After hydrotesting and reinspection, return the cylinder to service. Proceed to section 9E.
- C. If the cylinder has a feature or condition sufficient to condemn it, the inspection stops, and the condemning feature is recorded on THE FORM. Before recording what appears to be or may be a condemnable feature, we recommend that a qualified second or third inspector who is familiar with the visual inspection procedure, is consulted and asked to confirm the condition(s) which could condemn the cylinder. When it is agreed that the cylinder should be condemned, be sure that a signed Release Form<sup>f</sup> is on file from the cylinder owner. Proceed to section 9D.
- D. Procedures for handling a condemned cylinder:
  1. **In the USA:** Thoroughly review NOTE 7. After reviewing 9C above, we recommend that condemned cylinders in the USA are rendered unusable in one of two ways:
    - a. If the cylinder is condemned during this inspection and is to be returned by arrangement to Luxfer<sup>7</sup>, we recommend, in the USA, to strikeout the stamped markings on the cylinder crown (all-metal cylinders), leaving the serial number and hydrostatic test dates visible. If the cylinder is of a composite type, put a large "CONDEMNED" label on the composite portion of the cylinder (near to but not obscuring the original manufacturer's and other labels) and, using the repair epoxy, coat the 'condemned' label and seal it to the composite material. **Do not destroy the threads.**  
  
Contact Luxfer<sup>7</sup> to make arrangements for returning the cylinder to Luxfer.
    - b. If the cylinder is condemned during an inspection in the USA and is not to be returned to Luxfer,<sup>7</sup> we recommend that it (aluminum or composite) is made unusable by destroying all the threads to the extent that no valve or pressure fitting can be put into the cylinder opening (e.g., with a narrow chisel/screwdriver and hammer).
  2. **Outside the USA:** Cylinders used outside the USA should be condemned according to the specifications set by that country. If allowed and in accordance with the foreign specifications, do not damage threads on, nor drill holes in, those cylinders to be returned to Luxfer<sup>7</sup> in the USA.  
  
If a condition is found that would condemn the cylinder, then the inspection stops. After rendering the cylinder unusable, return a copy of THE FORM to the owner along with the condemned cylinder, any accessories, valve, etc. Do not attach any components to the condemned cylinder.
  3. Proceed to section 9E.

- E. Cylinders to be returned to service should have an inspection sticker or label<sup>6</sup> attached to the exterior, where the label doesn't obscure markings, other labels, or repairs:
  - 1. We recommend that all ACCEPTABLE cylinders be returned to service with an inspection sticker applied to the cylinder, indicating it has passed the inspection and is a safe and usable cylinder.
  - 2. We recommend the sticker includes information regarding any damage or imperfection the inspector has reviewed and/or any repair made by the inspector.
- F. Date and sign THE FORM. Return the cylinder and any accessories received with cylinder, and give the owner a copy of THE FORM and a copy of the Luxfer SCBA cylinder care and maintenance instructions.<sup>4</sup>

**NOTE: If the cylinder is acceptable and is to be re-valved, then continue on to Section 10 below before returning the cylinder and a copy of THE FORM to the owner.**

## 10 RE-INSTALLING VALVES

If the valve and valve components have passed inspection (from information obtained from the SCBA manufacturer), and if the cylinder has passed inspection, then the valve may be reinstalled as suggested below.

***CAUTION: SCBA components [like the valve and O-ring] are certified by regulatory agencies in the USA. DO NOT replace components without following the SCBA manufacturer's instructions. Replace components with parts that are authorized by the SCBA manufacturer.***

## 11 FILLING THE SCBA CYLINDER

The Luxfer SCBA cylinder can be filled and re-used for many years. If the SCBA cylinder is properly cared for and maintained and the recommendations in this Guide are followed carefully, your Luxfer cylinder will provide long, safe and reliable service. Your SCBA manufacturer will have provided you with instructions for the safe and proper filling of the SCBA cylinder. Carefully follow those instructions and the advice that follows.

In addition to your SCBA manufacturer's instructions on how to properly and safely fill your Luxfer SCBA cylinder, you must also be aware of and familiar with any and all filling guidelines, regulations, requirements and laws of the appropriate local, county, state/provincial and federal agencies. Many agencies, authorities and organizations have made rules and/or standards on how to fill and use SCBA cylinders.

In the USA, some of these agencies include, but are not limited to: NIOSH, OSHA, NFPA and DOT. Your state/province may have made rules for you to follow for the safe filling of SCBA cylinders with air. One such state is New Jersey and its agency, PEOSH. Some agencies (like PEOSH) regulate publicly owned/operated emergency response personnel safety. Such agencies may have rules that cover not only how to fill, but also requirements for personnel qualifications, equipment, inspections and safeguards, as well as the quality of the air to be used. You should always follow the rules and guidelines of the authorities with jurisdiction over respirators and their usage.

Similarly, know and be aware of any applicable industry or professional guidelines. Many organizations have issued guidance documents and standards covering the use and filling of SCBA cylinders. Contact any organizations that represent users of SCBA cylinders (e.g. firefighters) and obtain relevant guidelines.

This page is intentionally left blank.

## NOTES

1. At the time of printing, hydrostatic retesting and re-certification of SCBA cylinders is required in the USA every three or five years of the service life of the cylinder in interstate service. The USA Department of Transportation (DOT), through the Research and Special Programs Administration (RSPA) agency, issues retester's identification numbers to retest stations who may legally perform hydrostatic retesting. Only the DOT has the authority to issue such numbers in the USA.

RSPA issues station numbers (sometimes referred to as 'retester ID, or identification, numbers') based on the applicant meeting that agency's qualifications for same. Once issued, the number is valid for five years, provided the retest station maintains its equipment and personnel at the level required for the initial RSPA qualification. A third party, independent inspection agency, is charged with performing the applicant inspections.

A retest station must register with the DOT and obtain and hold a valid inspection station number in order to legally perform the hydrostatic retest on SCBA cylinders.

When a retest date is stamped on the cylinder (marking), or affixed to a composite cylinder (sealed with resin over it), the retest station is certifying that the cylinder meets DOT hydrostatic retest standards, and that the retest station holds a valid identification number, issued by DOT/RSPA. Every organization and cylinder owner should verify that the station where cylinders are being retested in their area is a duly qualified retest station holding a valid DOT/RSPA station number.

Information about hydrostatic testing and the retest program is found in the Code of Federal Regulations, Title 49, Section 173.34(e). Other documents may outline this program in more detail than found in this Guide. See APPENDIX F.

There are no specific testing and certification procedures outlined in 49 CFC for composite cylinders. Therefore DOT developed special tests and certifications, known as "exemptions."

All Luxfer high-pressure composite cylinders sold and used in the USA have a DOT exemption number. (Information on exemptions is found in paragraph 49 CFR 107.101). This is what is meant by "DOT authorized." Exemptions may vary according to the cylinder model. Such DOT authorized exempted cylinders are retested according to specific conditions and frequency written in the exemption. All DOT retest facilities performing retests on Luxfer composite cylinders must have a current copy of the cylinder's exemption and follow its instructions and conditions.

All DOT Luxfer exemptions specify that the retest be performed every three years on the composite SCBA cylinder and every five years on the all-aluminum SCBA cylinder. Both the cylinder owner and retest facility must know how often to have the retest performed.

Also, DOT authorized composite SCBA cylinders have a service life indicated in the exemption. If it has been fifteen years or more from the first hydro test date indicated on the composite cylinder, the cylinder must be removed from service.

The above applies to the USA, Canada and other DOT-compliant facilities. Other countries may have similar or different standards, requirements, and regulations controlling the use, handling and transportation of SCBA cylinders. If you are inspecting or operating outside the USA, you need to contact the authorities that



regulate SCBA cylinders to get: retesting, inspection and cylinder certification requirements.

Briefly, the hydrostatic retest is a measure on how much a cylinder will expand when a specified pressure is applied. In our opinion, the most common and safest method is the water jacket method. We would recommend that only a hydrostatic retest station using this method be allowed to test Luxfer SCBA cylinders.

The cylinder is placed inside of a water jacket or bath (containing water) which is specially sealed. The cylinder is pressurized and the amount of water displaced in the water jacket is measured by a precision method. This amount of water displaced represents how much the cylinder expanded under pressure and how much of this expansion is permanent after pressure is removed. Information is then gathered to determine if the expansion and permanent expansion of the cylinder complies with DOT regulations. If the cylinder passes, the retester marks<sup>g</sup> the cylinder by stamping into the metal the retester identification and the retest date or by resin-sealing a label<sup>g</sup> to the composite material. The cylinder is returned to service until the retest is required again or a condition warrants a retest.

2. Some SCBA owners may try to have SCBA cylinders partially filled with pure oxygen, then having them topped off with air or nitrogen (NITROX). This practice can cause catastrophic failure and loss of life or serious injury. SCBA cylinders, valves and other components are not specifically cleaned for oxygen use. Also, some lubricants used in the industry are not compatible with pure oxygen, or oxygen enriched air. This could result in a fire or rupture. Breathing air that contains more than 21 percent oxygen is generally referred to as "oxygen-enriched air." For additional information, or for guidance on the use of other gasses, oxygen, and various air combinations, contact the SCBA equipment manufacturer.
3. See your SCBA manufacturer for information about other available cylinder products.

4. SCBA technicians should ensure that users of SCBA cylinders understand the following general guidelines covering the care and maintenance of their Luxfer SCBA cylinder:

**CARE AND MAINTENANCE OF A SCBA**

**ALWAYS:**

- check for air leaks with each fill;
- keep the threads and cylinder interior dry and free from oil, dirt and other contaminants;
- fill cylinders with proper breathable air;
- follow the inspection recommendations (see above);
- follow valve manufacturer's installation procedures and recommendations;
- maintain all accessory equipment to your cylinder according to manufacturer's recommendations; and

**NEVER:**

- overfill cylinders;
- fill a cylinder if it leaks;
- fill a cylinder with a crack;
- ever completely discharge cylinder (except when you're planning to remove the valve) as it can lead to moist air seeping into the cylinder;
- fill or partially fill a cylinder with oxygen;
- artificially heat your cylinder;
- use a cylinder past its required retest date;
- use a composite cylinder past its allowable life (according to exemption);
- use a cylinder that hasn't been visually inspected according to its condition of use (see above);
- over-torque the valve;
- remove, obscure or alter manufacturer's labels or stamped markings; or
- use your cylinder in an extremely corrosive atmosphere or environment. If you do, always have the cylinder thoroughly visually inspected for damage before returning it to service.

**Here are some additional guidelines for SCBA cylinder users:**

**Maintenance** - After the use of an SCBA cylinder in an emergency or rescue operation, remove the harness assembly (backpack) and check for damage. Clean the cylinder and components. If water is used to clean, make sure all components are allowed to dry. Don't reassemble until all components are thoroughly dried. Do not apply heat over the temperature of steam (212°F/100°C) in order to dry a wet cylinder.

**Storage - Short term (Less than six months):** Tightly close the cylinder valve. Leave some pressure in the cylinder (about 25 psi). Secure the cylinder and assembly from rolling loose, tipping over or falling. Store at room temperature in a dry place, away from chemicals, artificial heat sources and corrosive environments.

**Long term:** Prior to prolonged storage, the valve should be removed from the empty cylinder. Wash the cylinder internally and externally with fresh tap water, then thoroughly dry (inside and out). Install the valve and O-ring according to SCBA manufacturer's recommendations. Replace the O-ring if the SCBA manufacturer recommends it. Store the valved cylinder at room temperature in dry conditions either upright or horizontal and properly protect the valve which could otherwise be damaged. Always store with some positive pressure inside the cylinder valve assembly (about 25 psi).

Never store a cylinder near heat or in a place likely to get artificially hot.

**Handling** - Cylinders should never be dragged, dropped, or roughly handled. When transporting cylinders, take steps to insure that the valve is protected and that the cylinder is well secured. SCBA cylinders should never be allowed to roll around loose, tip or fall during transport. Secure cylinders in a protected position.

**Painting** - Retouch damaged paint areas with air drying paint, but if damage has been done to the *cylinder metal or composite materials*, have it visually inspected first by an authorized technician. Never allow the cylinder to be heated in order to dry or cure paint. Never use corrosive, caustic, or acid paint strippers, burning techniques, or solvents, in order to remove paints from aluminum or composite surfaces. Any chemical used to remove paint from, or to paint an aluminum portion of a cylinder, should specifically say on the product label that it is safe and recommended for use on aluminum surfaces. (Then, in addition, such chemicals must not be allowed to come into contact with any composite portion of the composite cylinder.) If the entire cylinder is to be painted, contact Luxfer for recommendations.

**Inspections** - See earlier section on Frequency of Inspection (Section D).

5. There are several kinds of aluminum corrosion which differ by what caused the corrosion, as well as the shape and depth of the corrosion. First, refer to the Glossary<sup>c</sup> for the definition of '**corrosion**.' Next, refer to the Glossary<sup>c</sup> for the various corrosion-related words and phrases: '**broadspread corrosion, galvanic corrosion, line corrosion, pit corrosion**.'

Corrosion is one of the causes of material loss. Material loss may lead to leaks and ruptures of SCBA cylinders. As an inspector, you're asked to look at the cylinder, both inside and out (for cylinders with external aluminum surfaces), for corrosion. When you find corrosion, you are then asked to estimate the depth of the corrosion. In this way, you get an estimate on the material loss being caused by the corrosion.

Broadspread corrosion, sometimes called general corrosion, may be widespread on the cylinder surface, yet pose less of a concern than a corroded pit, which may go deep into the metal. FIGURE 9 shows some of the ways in which pit corrosion may

occur. Some types are clear, some pose a special problem for the inspector, since the pit may not go straight down into the metal. The corrosion may proceed at angles and in varying depths within the initial pit. Nonetheless, all types of corrosion must be inspected for how deep it has gone into the metal. See also PHOTOS 11 and 12.

6. As indicated in NOTE 5, corrosion is one of the causes of material loss. Material loss can also be caused by damage (cuts, dents, digs, gouges, scrapes, etc.) and some other imperfections. (See Glossary<sup>G</sup> for the definition of these terms and for the definition of '**imperfection**'). Once found, the location of the imperfection needs to be identified. Then, its depth needs to be estimated in order to compare with the acceptable limits.

Many of the acceptable limits are from the general limits established by the Compressed Gas Association (CGA). Others are from Luxfer's knowledge and experience with the Luxfer SCBA cylinder.

**Location:** Review FIGURES 1 - 4 to familiarize yourself with the various kinds of cylinder crown markings or labels you're likely to encounter. Review definitions of **markings** and **labels** in GLOSSARY.<sup>G</sup> SCBA cylinders manufactured by Luxfer have a mark in the crown (metal) or have a resin-imbedded label on the sidewall (composites). **Aluminum Cylinders:** All-metal cylinders usually have the mark "LUXFER." Looking from the top of the cylinder, down on the crown, put the "L" from the word "LUXFER" at the 12 o'clock position of an imaginary clock. **Composite Cylinders:** Use the right edge of the resin-imbedded original label (when normally reading it) to align at the 12 o'clock position of an imaginary clock.<sup>F3</sup>

All cylinder imperfections, damages, etc. can then be referenced by this location system no matter where in the world a Luxfer cylinder is used. For instance, if an external corrosion pit on an all-aluminum cylinder was located 90° from the "L" (to the right) on the sidewall, then the pit location is described as being at "3 o'clock, outside." RECORD on THE FORM that the pit was located at "3, outside," for an even more abbreviated entry.

If an external wall gouge was found just left of the "L" marking, it could be recorded as being at "11, outside."

Unless otherwise recorded, imperfections are assumed to be in the sidewall. Thus, other imperfections are recorded as located in the "crown", "base", "thread", "gland" or "face". If an internal crack in the shoulder<sup>P20</sup> of the crown was located at 270° from the "L" then its location is recorded as "9, inside crown."

Older (early '70's) all-aluminum cylinders may have a stamped Alcan symbol on them. Use it as the 12 o'clock position and record all imperfections and damage from this position. Other older cylinders may have an arrow symbol on the crown<sup>F4</sup> instead of the word "LUXFER." Use the arrow symbol for the 12 o'clock position.

Recording the position of all imperfections will help you to identify it later during future visual inspections; help you to show it to the owner at a later time; help you to show it to fellow inspectors and help you identify its location to Luxfer should it become necessary to have a manufacturer's representative review it. As you inspect a cylinder, take the few moments to identify the location of SCBA cylinder imperfections of concern and RECORD them on THE FORM.

**Depth Estimates:** It is important to next determine if the material loss located makes the cylinder unsafe to return to service, or whether the cylinder should be

inspected more frequently. To accomplish this, an estimate of the depth of the imperfection needs to be made.

Before proceeding, the cylinder surface (inside and outside) must be clean enough to see all imperfections. If corrosion is heavy or interferes with the good visual identification of pits, clean it away by one of the recommended cleaning procedures. See more on cleaning, NOTES 16 and 17.

Also, for gouges and digs on the external surface, disturbed, raised or upset metal may need to be filed even with a surrounding metal surface for good estimates of their depth. (See Glossary<sup>6</sup> and Section 4B above for the definition of 'upset metal'.)

Internal pits are 'measured' in depth by use of equipment designed to estimate the depth. External damage depth is best measured by the use of a depth gauge.

Estimating internal pit depths requires practice. Practice estimating the depths of depressions, pits, etc. using your pick and the Master Pit Reference Plate from your set of recommended inspection equipment,<sup>8</sup> as suggested at the end of this note.

See FIGURE 9 for examples of the different kinds of pit shapes and forms. When you probe inside of a corrosion pit, check it out carefully to be sure it doesn't hide deeper corrosion or corrosion at an angle. Let the pick slip into a pit or surface depression on the outside or inside cylinder surface and estimate the depression's depth. RECORD it on THE FORM.

When measuring the depth of broadspread corrosion, find the deepest pit within the corrosion or, if no pits are apparent, estimate the deepest part of the corrosion below where the normal cylinder surface would be.

RECORD all depth estimates with the corresponding location and the kind of imperfection.

**Practice with the Master Pit Reference Plate.** Get a feel for how far the pick enters a Plate depression and how that compares to the known depth of the Reference Plate depression. Lay the Plate flat and run the pick end of the pick/end probe along the surface around the depressions. Let the pick drop into one of the known depth depressions in the Plate. Compare the 'drop' you feel with the known depth of the Plate depression. Do this many times, with all the depressions in the Plate.

Next, once the pick is in a Plate depression, try to pull it sideways, out of the depression. Get a feel for how the different depths make it harder or easier to pull the pick out sideways.

Lastly, hold the Plate at an angle so you can't see the depressions. Slip the pick into, and pull the pick out sideways from, one of the Plate depressions that you can't see. Repeat this many times. Can you estimate the depth of the unseen Plate depression? Now look at the Plate depression you were practicing on, and check your accuracy. Practice estimating the depth again, changing the position of the Plate and sliding the pick into another 'unseen' depression. Repeat this until you feel confident and your accuracy is within one depression standard most of the time.

To restate the process you'll use on a cylinder: The way to use the pick/end probe for estimating the depth of pits, gouges, digs, etc. is to slide/push the pick over the undisturbed metal surface and then to let it fall or slip into the depression. Move the pick around in the depression, and then, by pulling and pushing the pick in and out

of the depression, you can get a feel of the pit's depth compared to the undisturbed metal surface around the pit. The deeper the pit, the harder it is to get the pick to come out by pulling it sideways. The more shallow the pit, the easier it is to get the pick to pull out sideways and the less noticeable the pick 'drops' into the pit when pushing it in.

Use of the depth gauge for external damage requires some practice, too. You can see by moving the depth gauge over the surface how positioning the gauge affects its reading. Being consistent with the positioning of the gauge improves its usefulness. For instance, when looking for the depth of a particular imperfection, first take readings around the imperfection where the metal or composite material isn't damaged.

When you take readings around an imperfection with the depth gauge, hold the gauge in the same orientation to the curvature of the cylinder. Then, when you measure the depth of the imperfection, hold the gauge in exactly that same orientation.

Depth gauge readings are not absolute. This means that the reading on the dial isn't the depth of the imperfection. Instead, you must take several readings in the area around the imperfection. Calculate the average reading you get in the 'good' areas. Now take a gauge reading at the imperfection. Finally, subtract the gauge reading at the imperfection from the average good reading. This difference gives you the depth of the imperfection.

7. Luxfer offers complete customer support for its SCBA product line. Many questions may be answered by visiting our web site at [www.luxfercylinders.com](http://www.luxfercylinders.com). For other concerns, questions, or problems, please contact the Customer Service Department as follows:

Luxfer Gas Cylinders  
3016 Kansas Avenue  
Riverside, CA 92507  
Telephone: (909) 684-5110  
FAX: (909) 781-6598  
[www.luxfercylinders.com](http://www.luxfercylinders.com)

Please be ready to identify any cylinder condition (damage, imperfections, folds, cracks, etc.) on which advice is sought. Have ready the serial number, cylinder identification, and all hydro dates (first and each subsequent). In some cases, Luxfer will request that condemned cylinders be returned for testing.

8. See FIGURE 6 for an example of a dental mirror and light. The dental mirror is common and standard whereas there are many different kinds of lights available. For use with a dental mirror, a small, bright penlight works well. The mirror is held to reflect the lit part of the threads or the inside of the crown of the cylinder. See PHOTOS 4 and 20 and FIGURE 6 for examples of mirror positioning.

These photos demonstrate how important the use of such a mirror is for the inspector. The mirror can 'see' areas the eye can't and, at the correct angle, may make a hard-to-see imperfection easy to identify. Careful use of a dental mirror may help determine the difference between a tool stop mark<sup>P10</sup> and a crack.<sup>P6</sup>

Almost all imperfections<sup>G</sup> require up-close observation that only a mirror and light will allow. There is one important exception, however. Tool stop marks are usually more readily seen from a distance. From a distance they appear as smudges or

shadows—an unclear vertical line across the cylinder threads. As your eyes get closer to the thread, a tool stop mark may get more difficult to see, or may even seem to fade.

Looking deep inside long cylinders requires a Light Wand or a high-intensity bulb on a long cord. See APPENDIX B for such equipment.

When an imperfection is found, see NOTE 6 for how to record its location and (if required) its depth.

9. Threads of both the cylinder and valve can trap debris. After wiping loose debris from the thread surface, wipe off as much of (if any is present) the lubricant as you can with a clean soft cloth. Never grind or press hard when wiping the threads as thread gall<sup>6</sup> may occur. Use an old toothbrush, bottle brush or other medium-hard bristled brush small enough to get inside the neck to clean the threads. Never use a brush with metal bristles. Dip the bristle end of the brush in some fresh isopropyl alcohol and brush the threads with this solution. Inspect the threads closely to be sure there is no debris left. The threads should be readily visible, showing imperfections clearly.
10. Finding a valley is a challenge. Finding a valley will require careful attention to detail. Lightly run the pick tool over the inside surface of the crown to ‘feel’ for valleys and depressions. They may be easier to feel than to see, so include this feeling technique along with your visual inspection of the inside surface of the cylinder crown. If you locate a valley, record its location first (see NOTE 6, “Location”), then continue. See FIGURE 7 and PHOTOS 16 and 17. Since the depth of a valley isn't a criteria for condemning a cylinder, the inspector doesn't have to estimate its depth, but be sure to RECORD its location.

Valleys that enter into the threaded area of a cylinder are a concern when they extend into the threads and reduce the number of continuous full threads below the limits set in this Guide, section 5B.

11. A wide variety of things have been found in cylinders by inspectors, including but not limited to: dead insects, dead animals, chemicals, fresh and salt water, corrosion, sand, dirt, and oil. Whereas most of the above may be recognizable from your life experience, there are materials found inside cylinders that you may not be familiar with and these include:

**Aluminum Corrosion:** Corroding aluminum may be white or black, or any combination of the two (e.g., gray). It is usually powdery after it falls away from the aluminum surface or it may cling to the aluminum surface as a raised, crusty material. With signs of corrosion on the surface, the powdery material of the correct color is usually easily identified as aluminum corrosion. A surprising large quantity of this material can accumulate, especially from cylinders not properly cared for and not inspected frequently.

**Aluminum Oxide:** A superior corrosion-resistant internal surface coating formed on Luxfer SCBA cylinders during the aluminum heat treatment process.

**Hydroxides:** This material often forms in aluminum cylinders stored with water inside. If conditions are right (poor maintenance and care of the cylinder), a light colored, whitish to gray aluminum oxide may be present which, when moist, becomes gummy. It is an alkaline material (like a strong soap) which may burn the skin.

When contaminating material is found inside the SCBA cylinder, it should be removed in order that the interior surface is visible for an accurate visual inspection. (See NOTE 17 for general cylinder internal cleaning procedures). Save some of the material to show the cylinder owner.

12. Through the decades that Luxfer has manufactured SCBA cylinders, there have been process/manufacturing changes. The cleaning and preparation of the cylinder inside surface processes have changed over the years, too. Some changes have occurred to improve the product internal surface, some have occurred to make the manufacturing more environmentally friendly. Whatever the reasons, the various manufacturing processes cause different visual surface effects. These differences are apparent when inspecting the interior of the cylinder.

Over the years, the interior of a just-manufactured Luxfer high-pressure aluminum and aluminum-lined SCBA cylinder may have had one of the following appearances:

- Bright shiny white/gray
- Gray to dark gray (almost black)
- Dark gray to brown
- Aluminum gray
- Aluminum gray with darker streaks

As the above surfaces are exposed to use, they may change in appearance. Most get darker over time. The recommended cleaning/drying methods<sup>17</sup> may make the surface more aluminum gray.

In all cases, the above list of possible surface appearances is 'normal' for the Luxfer SCBA cylinder.

13. Damaged composite materials can be repaired if the damage meets the criteria for repair (Level 2 damage) specified in this Guide. Determine if repair of the damage is allowed by following the criteria given in Section 4B. Measure the depth<sup>p28</sup> and length of the damage on the categorized cylinder (see CATEGORIZING THE CYLINDER above), and compare it to Section 4B criteria and the limits listed in its TABLE 1. In the case of abrasion<sup>6</sup> you will need to measure the area of the abrasion, then use the table and criteria in Section 4B above to determine if repair of the abrasion is allowed.

**Equipment and Supplies:** You'll need to have the following items in order to perform a repair, in addition to the empty damaged cylinder:

- a. A two-part, room temperature curing (fast drying) epoxy resin (each part of the resin system is in a separate tube or syringe-type dispenser) available from hardware stores;
- b. A stick (like a popsicle stick) or small stirring rod to mix the resin and help spread it on and around the damaged area;
- c. Mixing dish—a small shallow cup, cap or container to mix and hold a tablespoon of the mixed resin;
- d. Rag or old cloth for cleaning up; and
- e. A clean, protected work surface (bench or table) to bring the damage up to a convenient working height.



**Procedure:** Review PHOTOS 29 through 33. Only work with a depressurized, empty cylinder. Never attempt to repair a cylinder that is pressurized. Clean the cylinder surface on and around the damaged composite material. (See NOTE 16 for cleaning tips.) The surface must be dry and free of any chemicals, residues, oils, etc. Secure the cylinder on its side from rolling or moving around, setting the damaged area at the top.

Follow the repair resin mixing and preparation instructions on the package to make a total of about one tablespoon of mixed resin. Follow the repair resin instructions as to when the resin is ready to apply.

When the resin is ready, apply enough to the damaged surface to coat the area without running or dripping excess mixed resin. Spread the mixed resin in an area about one length or size of the damage beyond the damaged area. **For example:** If the damage is 0.75 inches long (19 mm), then the mixed resin should extend about 0.75 inches beyond each end and sides of the damage.

Allow the resin to thoroughly dry and harden. Have the cylinder hydrotested and reinspected prior to its next fill. Make sure to tell the hydrotester that it is a repaired cylinder and that, if the hydrotester is testing according to DOT requirements, he/she must use the criteria in the CGA pamphlet C-6.2 to accept or reject a repaired composite SCBA cylinder.

14. Learning the difference between a crack, scratch, breaks, and a tool stop mark in the threads is important in a visual inspection program. Study the photos for examples. See PHOTO 10 for an example of a tool stop mark which is sometimes seen during thread inspections. Contact Luxfer<sup>7</sup> for further help or answers to your questions. Review the definitions of these terms in the Glossary<sup>6</sup>.
15. Occasions arise in a cylinder's life that provide good opportunities for visual inspections prior to the minimum-period recommendation. For example, have a complete (internal and external) visual inspection done whenever the cylinder valve is removed (for any reason) and whenever the cylinder has been completely emptied.
16. The outside surface of a cylinder is cleaned so that the surface is exposed to the inspector's eyes. The surface finish on some Luxfer SCBA cylinders is a coating of paint. This can also include a clear coating over a brushed all-aluminum cylinder, or a clear coating over a wrapped composite cylinder. Luxfer may also supply SCBA cylinders to distributors who apply their own coatings. Also, some owners have their cylinder re-coated. Because of all these coating possibilities, there can be no generalized statement concerning Luxfer SCBA cylinder external surfaces.

The inspector must be satisfied that the exterior of the cylinder is clean enough to inspect the surface. Sometimes, this may mean removing dirt and oils. This can be done with any clean fresh water source or tap water. You can also use a soap solution made of one tablespoon of liquid dish detergent in one gallon of tap water, followed by many clean rinses, to remove dirt and oil. A light solvent tar remover may be used, followed by the soap solution and multiple fresh water rinses.

If, after cleaning the surface, the coating is seen to be raised or bumpy in places, then it is necessary for the inspector to look below the coating to determine if there is corrosion (metal) or chemical attack (composite). Some coatings may be removed in a small area simply by lifting a chip of it away from the surface.

## Aluminum Cylinders

If the raised paint is due to corrosion on the metal surface, it will most often be easily chipped off for an inspection. If corrosion is found on the exterior, under the coating, then the entire coating should be removed. Get permission from the owner before removing large quantities of coatings. See NOTE 4 for paint touch-up suggestions.

Any repainting of aluminum cylinders stripped of paint should be done with air-drying paints. Never use heat to dry or cure paints. Heating a cylinder may require that it be condemned and never used again. See NOTE 20.

Do not shot blast (other than sling type) the exterior of any Luxfer SCBA cylinder, or use any abrasive cleaners or abrasive cleaning methods. Any method, which may reduce the metal thickness or create metal loss, should not be used to clean Luxfer SCBA cylinders.

## Composite Cylinders

If the raised paint (that is, paint which is lifting off the composite surface) is due to chemical action in or on the composite material, the cylinder is to be condemned.

No paint stripping or chemical removal of paint from composite surfaces is allowed. Touch-up paints can be applied, but the retouch must not hide any repaired surface areas.

17. Luxfer aluminum SCBA cylinders may never need an internal cleaning, provided they are cared for and maintained according to manufacturer's recommendations.<sup>4</sup> Occasionally, lubricants (which are all not recommended) may get into the cylinder or organic materials may be trapped, causing odors. Under these circumstances, when the cylinder has been contaminated, an internal cleaning is useful. This cleaning is a general cleaning guideline for removing offensive odors, lubricants, and light grime from an otherwise empty cylinder:

**Moisture and light grime:** Steam clean and blow dry.

**Oil, grease, lubricants, light corrosion:** Clean with a mild soapy solution (one tablespoon of hydro-carbon free liquid or solid hydro-carbon free detergent to one gallon of tap water (use soft water if the tap water is hard)). Rinse several times with tap water, rinse twice with soft water, steam clean and blow dry.

**Odors:** Rinse thoroughly with a solution of baking soda (one cup baking soda to one gallon of tap water). Rinse with clean tap water. Then, rinse with a solution of vinegar (one half (1/2) cup of household vinegar to one gallon of clean tap water). Rinse several times with fresh tap water, rinse twice with soft water. Steam clean and blow dry.

Do not shot blast (internally or externally) or use any abrasive or corrosive cleaners, or abrasive cleaning methods on a Luxfer cylinder, other than the above recommended procedures.

18. Label removal from the coated surface (painted surface) of an aluminum Luxfer SCBA cylinder should be done so as to not disturb or ruin the coating. A particularly good physical label removing tool (the Super Scraper) is available from Motsenbocker. See APPENDIX B for a definition and APPENDIX C for sources. We do not recommend the use of chemical label removers. Do not attempt to remove a resin-embedded label.

19. Some chemicals are known to cause damage to composite materials. The list would be too long to put in this Guide, however, we can list the types of chemicals that are known to cause damage, attack, or harm composite surfaces.

**Any cylinder composite material coming into prolonged (e.g. soaking) contact with these types of chemicals and materials must be condemned:**

- Solvents: (paint thinners, kerosene, turpentine, paint solvents, paint cleaners, all paint-like products, stoddard solvent, epoxy solvents, resin removers, organic solvents, etc.);
- Vehicle Fluids: (materials that contain benzene, glycol (anti-freeze), battery acids/alkalis, window washer fluids, oils containing solvents, flammable materials, organic volatile materials, gasoline and oil additives, fuels (gasoline, gasohol, methanol, etc.);
- Strong Bases: (materials that contain medium to high concentrations of: sodium hydroxide, potassium (and/or other) hydroxides, materials that contain strong soap solutions, cleaning (soap) solutions, etc.);
- Acids: (materials that are or contain any concentration of acids like hydrochloric, sulfuric, nitric, phosphoric, acetic acid (vinegar), etc.);
- Corrosives: (materials that contain corrosive components or that are corrosive themselves, such as the chemicals mentioned above and: cleaners, glass cleaners, metal cleaners, resin cleaners/removers, drain openers/cleaners, glues, rubber and other chemical cements, and atmospheres containing corrosive gases); and
- Alcohols: (materials that are or that contain any type of alcohol).

Avoid cleaners, and do not allow composites to come into contact with cleaners that are not specifically recommended for cleaning in this Guide. See NOTES 16 and 17.

20. As a general rule, aluminum cylinders exposed to temperatures in excess of 350°F (175°C) must be condemned (see CGA C-6.1). This is because the properties of the aluminum metal rapidly reduce when temperatures exceed 350°F (175°C), and the longer the exposure the greater the degradation of the metal. The higher the temperature above 350°F (175°C), the faster and greater the degradation. It is a combination of temperature and time that is critical.

But firefighters can wear aluminum and composite SCBA cylinders with complete confidence even though they are frequently exposed to temperatures in excess of 350°F (175°C). A firefighter is never exposed long enough to excessive temperatures to damage the cylinder's metal properties. Even wearing the typical firefighting protective equipment, a firefighter will feel sufficient discomfort from life-threatening heat and pull back before his or her cylinder could be affected by the exposure to that excessive temperature.

Luxfer's concern, and yours too, is over the SCBA cylinder left in a fire unattended. Such cylinders must be condemned. For further information about heat exposure, read Luxfer's Technical Bulletin on the subject. Contact Luxfer<sup>7</sup> for a copy.

21. All references in this Guide to 'inspection' refer to the comprehensive internal and external visual inspection outlined in this Guide. This 'visual inspection' must not be confused with that of any regulatory authority. Quite often, a regulatory authority will require the inspection of SCBA before and/or after each use or on a frequent basis. For instance, OSHA in the USA requires frequent inspections of SCBA in CFR 29, Part 1910.134(f)(2). These types of inspections generally mean an external visual inspection of the equipment and does not include the disassembly of the SCBA cylinder for internal inspection. When 'inspection' is used in this Guide, it means the 'thorough external and internal visual inspection' outlined and recommended in this Guide, unless it is stated otherwise.
22. The frequency of cylinder use and type of service are estimated. No documented data or cylinder record is needed for each cylinder so as to be able to estimate the frequency of filling or topping off of an organization's SCBA cylinder inventory. An experienced and knowledgeable member of the organization may estimate the frequency of use and the type of service of their SCBA cylinders . This estimated frequency will determine the frequency-of-use rate for all cylinders belonging to that organization.<sup>6</sup>

This page is intentionally left blank.



# APPENDICES

## APPENDIX A

### VISUAL CYLINDER INSPECTOR TRAINING WORKSHOPS

Luxfer recommends that anyone who wants to perform thorough external and internal visual inspections on SCBA cylinders, obtain training and accreditation from a reputable and knowledgeable source. The guidelines set forth in this document are not meant to replace the experience and knowledge an inspector can obtain from an inspection training course. At this time, we are aware of the following independent source for such training:

Professional Scuba Inspectors, Inc. (PSI)  
6531 NE 198th St.  
Seattle, WA 98155  
(425) 486-2252  
[www.marinestudio.com/sunpacific/psi](http://www.marinestudio.com/sunpacific/psi)  
e-mail: [psicylinders@msn.com](mailto:psicylinders@msn.com)

There may be other training agencies offering visual inspection training courses and materials. We suggest you contact your SCBA manufacturer, trade or industry association for further information.

# APPENDIX B

## INSPECTION EQUIPMENT AND ACCESSORIES

Equipment, tools and accessories referred to in this document may be available from multiple sources. This appendix identifies and lists recommended inspection equipment tools and accessories.<sup>21</sup> Purchase sources are given in parentheses at the end of each product description. These sources are listed in APPENDIX C.

**Pick/end probe:** Extends inspector's eyes and fingers into cylinder to probe imperfections of the interior surface. Looks like a long-handled (30 inch) dental pick. Used to estimate depths of corrosion pits and external damages (gouges, digs, scrapes, etc.). (1, 5)

**Straight Probe:** The long-handled (30 inch) probe extends the inspector's eyes and fingers far into the cylinder to probe the inside base. This is a straight, pointed-end, thin, stiff metal rod. (1, 5)

**Master Pit Reference Plate:** A very useful reference disc. This round disc has ten or so machined depressions in it of known depths. Depths should range from 0.01 inch to greater depths, including the depths to use with this guide. More depths/pits on the reference plate are acceptable. With practice, this plate will give the inspector a sense for estimating imperfection depths in cylinder surfaces. (See the end of NOTE 6 for recommended use and see Glossary<sup>6</sup> for definition of 'imperfection'). (1, 5)

**Dental Mirror:** A typical high quality, half-inch diameter mirror, placed at the end of a bent probe, commonly used in dental offices. Used here to inspect the thread and internal crown area of the cylinder. The preferred dental mirror is one which offers a 2X magnification of the reflection, manufactured by Grobet File Company of America, part 29.386 (ask for the magnification mirror, same part number). Review the photos to see how indispensable this tool is in viewing hard-to-see areas of the cylinder. See FIGURE 6 for a sample positioning of the mirror when looking for shoulder cracks, and PHOTOS 4 and 7 for thread inspection positioning. (1, 5, 6)

**Inspection Light:** A small, penlight-like light source (see FIGURE 6). The light is used in conjunction with the mirror. Variations on this theme have proven useful, such as the custom-altered Mighty Lite from source 1. (1, 5, 7)

**Light Wand:** For seeing deep into the cylinder, it is more useful to have a light source that can enter the cylinder and go to the base of the cylinder. Consider investing in a wand or inspector's lamp. This can be as simple as a string of white Christmas tree mini-lights on a stiff rod or as elaborate as a high-intensity bulb at the end of a flexible cord. (1, 5, 10, 12)

**Magna-Lite:** Hand-held magnifier with light source. Useful for inspecting the outside surface areas of the cylinder. See FIGURE 5. (5)

**Visual Plus:** A non-destructive testing (NDT) device made by Advanced Inspection Technology to automatically detect shoulder and thread cracks. A sensitive device that, when used properly, gives excellent and reliable determinations on whether or not shoulder/thread cracks or other neck-area imperfections are present. (14)

**Dow Corning 111:** Lubricant of choice for installing valves to cylinder. A little goes a long way. See Section 9. (1, 2)

**Small Metal File:** A fine metal file is used to remove raised portions of disturbed metal on the exterior of the cylinder. (5)

**Work Bench:** A steady, well-lit table or bench to bring the cylinder to a comfortable height for external inspection. Cylinder should be braced with blocks or a vise that

doesn't damage the cylinder surface. Another station to inspect the interior of the cylinder is useful, at about knee level to the operator.

**Inspection Stickers:** The inspector's own design (or ones obtained from an outside source) with a place for the date inspected and the inspector's initials/name. Sticker should indicate "ACCEPTED" and where the inspection took place. (1, 5)

**Old Tooth Brushes:** You now have a use for those old toothbrushes you've been throwing out. A medium-firm brush or bottle brush will do just as well when cleaning cylinder threads. Never use brushes with metal bristles. (5)

**Isopropyl Alcohol:** Sometimes referred to as 'rubbing alcohol,' and is readily available. Read the label carefully to make sure it is isopropyl alcohol. Used only to clean cylinder and valve threads. See NOTE 9. Alcohols must not come into contact with composite materials.<sup>19</sup> (5)

**Liquid Dish Soap:** Used to clean the exterior<sup>16</sup> and interior<sup>17</sup> of dirty or contaminated cylinders. Obtain and use a mild, non-ammonia soap that is hydro-carbon free.(5)

**Air-Dry Paints:** To touch up external surfaces opened for inspection (e.g., small area paint removal where corrosion under the coating is suspected but found not to be dangerous), or for touching up gouges, digs, etc. which have only removed or disturbed the external coating. Paint must be labeled that it is recommended for aluminum and composite surfaces. See NOTE 4 for more information about painting as it pertains to the proper maintenance of the cylinder. Never paint over repairs (composite cylinders) or any damaged areas (all types of cylinders) that affect material loss. Before repainting, contact Luxfer<sup>7</sup> for a current technical bulletin on repainting cylinders.(5)

**Bowls:** Sturdy ones, used to catch water, debris and contaminants found inside cylinders.

**Super Scraper:** Remove labels physically by slipping this thin plastic wedge under the label but on top of the coated/painted surface. Useful for removing labels from aluminum surfaces which may hide external imperfections<sup>6</sup> on aluminum surfaces.(8)

**Scotch-Brite Scrubbing Pads:** A non-abrasive scrubber for removing stuck-on dirt and debris from aluminum cylinder surfaces. (5, 9)

**Documents:** Customer Release for Cylinder Inspection Form.<sup>F</sup> A two-part Form<sup>D</sup> for recording inspection information. Previous inspection reports on the cylinder being inspected if available, or from the inspector's files. (1, 5)

**Filing System:** Keep records of previous cylinder inspections and inspection reports. Keep records of fillings, also. (5)

**Straight Edge/Ruler:** A reliable straight edge of metal or wood, together with a small ruler with easy-to-read increments, is needed to measure cylinder imperfections and damage(s).

For inspectors who will likely be having to clean the interior and exterior cylinder surfaces of dirt and contaminants, a steam cleaner and dry, warm air source is recommended.

**Depth Gauge:** The depth gauge mentioned in this Guide refers to a homemade tool. It is used to measure the relative depths of cuts, scratches, pits, and abrasions on composite cylinder external surfaces. Purchase a dial depth gauge, mount it on a pair of small, narrow rails that are curved to fit the curvature of the composite cylinder. See PHOTO 28. A commercially available type of depth gauge used to measure pits in piping is available from reference 13. (3, 11, 13).

**Items of general usefulness:** Clean, dry soft rags, clip board, pens/pencils, and a hand-held magnifying glass. (5)



# APPENDIX C

## INSPECTION ACCESSORY SOURCES

These sources for the equipment and supplies listed in APPENDIX B are not meant to be exclusive. Other suppliers may be closer to your facility and offer acceptable inspection<sup>21</sup> aids.

1. PSI, 6531 NE 198th St., Seattle, WA 98155, (425) 486-2252. A good source of inspection equipment and literature (publishers of *Inspecting Cylinders* by William L. High). PSI specializes in inspection training and inspection equipment, and is referenced many times in APPENDIX B.
2. Dow Corning 111 Lubricant may be found in your area by looking up BEARINGS in your Yellow Pages/Phone Book. Contact bearing suppliers in your area to see if they sell it. The lubricant is used in the bearing industry, so if it is not available from a local bearing company, one may help you find it. Also available from source 1 above.
3. The depth gauge mentioned in APPENDIX B and NOTE 13 can be easily made. Purchase components from source 11. Have a machine shop do the work if you are not equipped to do it at your facility. A dial depth gauge is mounted on small, narrow 'rails' to fit the curvature (arc) of the cylinder. See PHOTO YY. (5, 11)
4. Galiso Nuvac, 22 Ponderosa Dr., Montrose, CO 81402, (800) 854-3789.
5. General supply or manufacturing places (local and mail order), such as: hardware store, grocery store, drug store, office supply, printer (stickers), laboratory supply houses, scientific supply sources (e.g., Van Waters & Rogers (800) 999-8974, Baxter Diagnostics Inc. (800) 234-5227, etc.), and local machine shops (picks, probes, 'homemade' Master Pit Reference Plate, Light Wands, tumbler, etc.).
6. Ken's Tool & Supply, (909) 686-2542; Wherever you purchase the dental mirror, ask for the half-inch, 2X mirror manufactured by Grobet File Company of America, part number 29.386. The part number doesn't guarantee the magnification of the mirror. You'll need to ask for the 2X mirror with that part number.
7. PB-2 Penlight, Mel's Industrial Supply, (909) 737-8143. Many office supply stores and hardware stores have such lights.
8. Motsenbocker Super Scraper. Call (619) 581-0222 for your nearest supplier.
9. 3M Corporation product. Check sources listed in source 5 above.
10. Hydro-Test Products Inc., 1-800-225-9488.
11. Starrett (714) 879-6637 for engineering tools and supplies.
12. ZTC, Inc., 1-800-882-0708.
13. W. R. Thorpe & Co., P. O. Box 38, Ketchum, OK 74349, 918-782-2003. Ask for information about "Pipe Pit Gages."
14. Advanced Inspection Technology, 1220 E. Washington St., Suite 24, Colton, CA 92324-6436, (909) 369-0945.

# APPENDIX D

## SCBA CYLINDER VISUAL INSPECTION FORM

You may want to use the following sample form. Feel free to modify or copy this form. Pre-printed forms are available from PSI and other sources (see APPENDICES B and C).

Ideally, you may want to print the guidelines for the care and maintenance of the cylinder (as set out in NOTE 4) on the back of THE FORM.

## SCBA CYLINDER VISUAL INSPECTION FORM

Cylinder Owner: \_\_\_\_\_  
Phone: \_\_\_\_\_ Date: \_\_\_\_\_  
Address: \_\_\_\_\_  
City: \_\_\_\_\_ State: \_\_\_\_\_ Zip: \_\_\_\_\_

### I GENERAL

Receipt: With accessories \_\_\_\_\_  
Under pressure/any leaks? \_\_\_\_\_

### II CYLINDER INFO

Markings: Serial Number \_\_\_\_\_ Thread: \_\_\_\_\_ Service Pressure: \_\_\_\_\_  
Gov't. Specification/Identification: \_\_\_\_\_ Category: \_\_\_\_\_  
Original Hydro: \_\_\_\_\_ Last retest: \_\_\_\_\_  
Visible conditions/reason for inspection? \_\_\_\_\_  
Inside contaminants/materials found/odor: \_\_\_\_\_

### III EXTERIOR

Any bulges, or bows noted? \_\_\_\_\_ Where? \_\_\_\_\_  
Any dents, cuts, digs, gouges, abrasion, scratches? \_\_\_\_\_ Where/depth/length: \_\_\_\_\_  
Corrosion? \_\_\_\_\_ Kind? \_\_\_\_\_  
Where/depth/length: \_\_\_\_\_

### IV THREADS

Gall? \_\_\_\_\_ Known leaks? \_\_\_\_\_ Good thread count, starting from top: \_\_\_\_\_  
Good threads needed? \_\_\_\_\_ O-Ring gland/face condition: \_\_\_\_\_ Cracks? \_\_\_\_\_  
Where/describe: \_\_\_\_\_ Valleys into threads? \_\_\_\_\_  
Where? \_\_\_\_\_ Thread loss due to valley? \_\_\_\_\_  
How many threads affected? \_\_\_\_\_ General appearance: \_\_\_\_\_

### V INTERIOR

Cleaning required? \_\_\_\_\_ Type? \_\_\_\_\_ Crown cracks/folds found? \_\_\_\_\_  
Where? \_\_\_\_\_ Corrosion? \_\_\_\_\_ Type? \_\_\_\_\_  
Where/depth/length: \_\_\_\_\_

### VI CYLINDER STATUS

Accept/Repair/Condemn: Explain: \_\_\_\_\_  
\_\_\_\_\_  
Condemn how? \_\_\_\_\_  
Remarks: \_\_\_\_\_  
Inspector's signature: \_\_\_\_\_ Location: \_\_\_\_\_  
Inspection Date: \_\_\_\_\_

# APPENDIX E

## OWNER RELEASE FOR CYLINDER INSPECTION FORM

You may want to consider using the following sample form. Feel free to modify or copy this form. Pre-printed forms are available from PSI and other sources (see APPENDICES B and C).

### OWNER RELEASE FOR CYLINDER INSPECTION FORM

#### *To Our Valued Cylinder Owner and Customer:*

Thank you for considering us for your high pressure SCBA cylinder visual safety inspection. The regular visual safety inspection of your SCBA cylinder is part of its routine care and maintenance. With proper care, maintenance, regular visual inspections and hydrostatic retesting, your cylinder will provide you with a long, safe and satisfactory service.

Visual safety inspections need to be done on your Luxfer SCBA cylinder to assure its continued safe service. The frequency of these inspections depends upon the kind of use, care and maintenance your cylinder gets. The more often it is used, the worse its care, maintenance and handling, and the more frequently it should be inspected.

Your cylinder should also be inspected before further use whenever it is known to have been exposed to temperatures over 350°F, in an accident, known or suspected to be leaking, has been dropped, has fallen, has been struck, has obvious metal corrosion since the last visual inspection, has composite material damage or chemical exposure, has a gouge, dent, scrape, cut, dig or in any way has been damaged since the last visual inspection, or was stored with water, material or matter inside the cylinder.

Your cylinder should not be used if it is, or is suspected to be, leaking.

Your cylinder should be inspected once every thirty months, or more frequently in certain cases. The visual inspector can help you decide how frequently your cylinder should be inspected. If it is time or if you suspect or have any concern about the general condition of your SCBA cylinder, a visual inspection by an experienced visual inspector is needed.

The visual inspection is a safety check on your cylinder, and the inspector performing it wants to make sure that your SCBA cylinder is safe for continued service. If, during the inspection, a cylinder condition exists which would make your SCBA cylinder unfit for continued service, it will be necessary to condemn and to render your cylinder unusable. The condemned cylinder, valve, and accessories will be returned to you with an explanation of the condition found. By signing below, you agree to this process which may render your SCBA cylinder unusable in the future.

I, \_\_\_\_\_ (print owner name or name of authorized owner representative), have requested that the SCBA cylinder identified by the serial number: \_\_\_\_\_ be visually inspected.

I agree, as a condition of having this visual inspection, that the cylinder may be disabled and/or rendered unusable if it does not meet the accepted standards of quality established by the manufacturer for continued service. I will receive a written report of any and all conditions which caused the SCBA cylinder to fail the inspection and to be condemned. Also, I will have the condemned cylinder, accessories, components, and valve returned to me.

Owner (or representative's) Signature: \_\_\_\_\_ Date: \_\_\_\_\_

Witnessed by (inspector or station rep.): \_\_\_\_\_

## APPENDIX F

### FURTHER REFERENCES AND INFORMATION

For further information and reading, we suggest reviewing the following documents. CGA Pamphlets: C-6.1 (aluminum cylinders) and C-6.2 (composite cylinders) are required reading.

CGA Pamphlet C-6.1; "Standards for Visual Inspection of High Pressure Aluminum Compressed Gas Cylinders,"

CGA Pamphlet C-6.2; "Guidelines for the Visual Inspection and Requalification of Fiber Reinforced High Pressure Cylinders,"

Other CGA Documents: C-1 (Hydrostatic Testing information); and C-7 (Compressed Air information)

all published by Compressed Gas Association, Inc.:

1725 Jefferson Davis Hwy, Suite 1004  
Arlington, VA 22202-4100  
(703) 412-0900

Department of Transportation, Title 49 Code of Federal Regulations (CFR) Parts 100-199, (obtain current publications) from:

U.S. Department of Transportation  
Superintendent of Documents  
U.S. Government Printing Office  
Washington, DC 20402

Inspecting Cylinders, by William L. High.

Available from:

PSI, Inc.  
6531 NE 198th St.  
Seattle, WA 98155  
(425) 486-2252

Luxfer SCBA Cylinder Exemptions:

DOT-E 7235  
DOT-E 9894  
DOT-E 10345  
available from:

Associate Administrator for Hazardous Materials Safety  
Research and Special Projects Administration  
Department of Transportation  
Washington, DC 20590  
Attn.: DHM-31

This page is intentionally left blank

# APPENDIX G

## GLOSSARY OF TERMS

These terms are defined and described as they relate to Luxfer high pressure SCBA aluminum cylinders.

**abrasion:** When used to express a damage condition on composite materials, it means the type of damage caused by wearing, grinding, rubbing away by friction, or scraping of the composite material. These types of damage can be caused by sliding contact with a rough surface. Inspection criteria for abrasion includes the depth and area of the region.

**aluminum alloys:** SCBA cylinders manufactured from aluminum are actually produced from a variety of aluminum mixtures. These mixtures are called alloys. An alloy called 6351 was used by Luxfer up to and including 1987. Since 1988, Luxfer uses an alloy called 6061.

**area:** The inspector will need to be able to calculate the 'area' of damage to apply the inspection criteria to abrasions and dents in composite materials. (See **abrasion** and **dent** in this Glossary).

**base:** The bottom, flat portion of the aluminum cylinder. Also, the rounded end of a composite cylinder that has no opening. See Figure 11.

**bow:** A cylinder exhibiting a curved feature. On one side, the cylinder may appear to be raised, as in PHOTO 18. On the other side, the cylinder may appear to have a depression, as in FIGURE 11. Such a cylinder usually has a peculiar, un-smooth pitch when it rolls on a flat surface. Also known as "banana."

**broadspread corrosion:** General corrosion, usually irregular, covering a relatively large area and causing aluminum material loss. May or may not have random pitting and is sometimes difficult to see when it is uniform. Also called general corrosion, or wide-spread corrosion.

**bulge:** A swell or bend outward of metal or composite material. A protuberance which is easy to see using a straight edge. See Figure 10.

**composite material:** Used in this Guide to mean the resin and wrapping fiber system or systems applied to aluminum-lined SCBA containers. It is beyond the scope of this Guide to describe the differing resins and fibers and systems employed to manufacture the Luxfer composite SCBA cylinder. Unless otherwise written, the entire Luxfer Gas Cylinder family of composite material cylinders used in the SCBA service and referred to in this Guide are grouped into the 'composite cylinder' category.

**condemn:** To remove from service and make unfit for future use. The Luxfer SCBA Visual Inspection Guide indicates when to condemn a cylinder and, in Section 9E., indicates how to condemn a cylinder.

**continuous full thread:** Uninterrupted, unbroken thread with a sharp peak and without imperfections. (See thread and imperfection).

**corrosion:** The simple oxidation or galvanic action of aluminum metal. Action of chemicals, salts, water, or sea water may produce corrosion if the cylinder isn't kept clean and dry, or taken care of properly. Corrosion caused by galvanic action often comes from the exposure of the cylinder to other metals. (See **galvanic corrosion**). Copper, brass and stainless steel contacts are significant sources of galvanic corrosion of aluminum.

Most valves are brass, plated with an inert metal (e.g., chromium or nickel), however, if the plating is broken, incomplete or penetrated, the valve brass in contact with aluminum may cause galvanic corroding of the aluminum. This type of galvanic corrosion occurs primarily around the valve connection area, but may spread throughout the cylinder interior.

When stainless steel comes into contact with the aluminum cylinder or liner (for instance, when steel accessories, straps, bands, etc. remain in contact with uncoated or unprotected aluminum external surfaces), galvanic corrosion can occur.

Corrosion leading to material loss may cause cylinder leaks and ruptures.

Corrosion of aluminum will appear as a white-roughened or discolored area, with a loose or crusty white deposit sometimes associated with the corrosion. Estimating the material loss due to the corrosion, and condemning cylinders with severe or unacceptable corrosion is an important function of the inspection procedure. See **broadspread corrosion**, **line corrosion**, and **pit corrosion**. Proper care and maintenance will prevent corrosion. See NOTE 4.

**crack:** A split or fracture (usually jagged) in the metal causing an open and often fine fissure which may cause leaks if permitted to develop. Carefully inspecting for cracks is an important function of the inspection procedure. Condemn all cylinders with cracks in the aluminum before any leak or rupture can occur. See also **thread cracks**. For a discussion of 'crack' as it pertains to composites, see **delamination**.

**cross threads:** When the threaded area appears to have two different sets of threads. This can be caused by installing the wrong valve (threads on valve don't match the threads in the cylinder) or by installing a valve crookedly. When a valve is screwed in crookedly or the wrong valve is forced into a cylinder, the valve threads can 'cut' a new set of threads in the cylinder threading. The new set or partial set of threads are there, in addition to the set of threads machined there by Luxfer. The visual effect is to make the threaded area appear to have two sets of threads. A cylinder with cross threads must be condemned.

**crown:** The dome-shaped top portion of the cylinder which includes the distance between the top facing down to where the sidewall begins. The aluminum in this area is thicker than in the sidewall on all aluminum cylinders and hoop wrap cylinders and is more tolerant of damage. But, in composites the crown/dome and base that is composite-wrapped is less tolerant of damage. See FIGURE 5 and TABLE 1.

**cut:** An incision or gash associated with some loss of wall thickness in the aluminum, or associated with some loss of strength in composites, usually made by a sharp object.

**cylinder:** For the purposes of this Guide: A single-piece tank made of aluminum alloy material or a hoop-wrapped composite/aluminum container manufactured by Luxfer to contain air under high pressures for use in a self contained breathing apparatus (SCBA). The cylinder is only the tank portion of the assembly and does not include any attachments.

**depth gauge:** A 'dial depth gauge' available from many engineering supply companies, is mounted on a pair of small, curved rails to roughly match the curvature (arc) of the cylinder and becomes a 'depth gauge.' This device is used to estimate the depth of external damage done on composite materials. The dial should read in increments of at least thousandths of an inch (0.001 inch – 0.025 mm), to relatively measure the depth of a cut or scratch on the composite material. See PHOTO 28.

**delamination:** The separation of layers or strands of wrap/fiber materials from other layers or strands. The effect is to appear like a crack along the direction of the wrapped fibers. Closer inspection may show loose fiber strands. On the composite portion of a cylinder with delamination, the strands may not be cut, but they could be loose and separated from other strands.

When layers of fibers separate, they may appear 'frosty' under resin-coated composite materials. Loose strands are cause for condemning. Small frosty areas under resin-coated composites may be acceptable. Refer to inspection guidelines.

**dent:** Imperfection of the cylinder caused by a blunt object in such a manner that the wall (aluminum or composites) suffers no material loss but shows an indentation or evidence that the container was dented.

Dents up to one sixteenth of an inch deep in the aluminum can be tolerated when the major diameter of the dent is two inches or more. The condemning criteria is thus: Condemn cylinders with dents over one sixteenth of an inch in depth; condemn cylinders with any depth dent if the dent diameter is under two inches. See PHOTO 1.

The dent criteria for exterior aluminum metal may seem confusing. Small diameter dents create a greater damage to the metal than large diameter dents. This is because the small diameter dent has actually deformed the metal at a greater 'angle' than if it were a large diameter dent. It is this degree or severity of the deforming angle which renders the metal potentially unreliable. Large diameter dents spread this angle over a larger surface and thus, that degree of angle is small (the dent is less of a concern).

Dents in composite materials may cause delamination or separation of fiber layers from one another. The appearance of this to the inspector is an area in the composites that is 'frosty' or opaque. Dents or frosty areas in composites may be cause to condemn the cylinder. The criteria for composite dents is based upon the area of the frosty region. See the criteria, section 4A. Also, an aluminum-lined composite cylinder may show evidence of a dent by looking at the liner from the thread opening. See interior inspection, Section 6B.

**digs:** An imperfection associated with some loss of wall thickness (material loss) usually caused by a sharp object, leaving a gouge-like short, wide cut.

**DOT:** Department of Transportation. A federal agency regulating interstate trade within the United States of America. Wherever references to the DOT are made, the inspector and reader of this document should be aware that other countries may have similar or differing regulations. If operating outside the USA, the inspector must be aware of regulations in the country the cylinder is used, which govern cylinder safety, care, handling, use, certification, inspection, and filling. See APPENDIX F.

**exemption:** The USA DOT issues exemptions for all Luxfer composite cylinders. The exemption gives retest information as well as cylinder life. All retesters, cylinder owners and inspectors should be aware of any and all exemption requirements pertaining to the composite cylinder(s) they handle.

**face:** The topmost surface of the cylinder, parallel with the base, above the threads, which may touch the bottom of an installed valve. See FIGURE 5.

**fold:** The place where two metal flows meet in such a manner as to create a sharp, visual groove. The groove of the fold will always be along the length of the cylinder and usually in the crown area. See FIGURE 8 and PHOTOS 14 and 15.



**Form, The:** The SCBA Visual Inspection Form (see APPENDIX D for an example) or any form or cylinder log used to record cylinder information, owner information, the inspection date and results, and the inspector's name and findings. If the cylinder is inspected by the owner (for example at the station that owns it), then it would be more practical to maintain a cylinder log (electronic and/or hardcopy) for the life of the cylinder.

**full thread:** A sharp thread which is continuous for one complete turn (360°) around the neck, without cracks, nicks, or distortions interrupting the thread.

**gall:** An imperfection in the metal's surface including a scratch, small gouge, or raised metal areas. Gall in SCBA cylinders is a concern when located in the thread and/or O-ring gland areas. See **thread gall** for more detailed information.

**galvanic corrosion:** Corrosive action caused by an electric current flow between metals, normally in a wet environment. An electric current is often formed between aluminum and copper (and copper alloys, like brass), and aluminum and stainless steel. Brass valves must be properly and thoroughly plated with metals which are more inert (e.g., chrome and nickel). Keep uncoated steel accessories (straps, bands, etc.) from coming into contact with uncoated/unprotected aluminum. See **corrosion**.

**gouge:** An imperfection associated with some material loss usually caused by a sharp object leaving a wide and usually deep trough in the metal or composite material. See PHOTO 2.

**government specification:** A government's requirements for a cylinder which is usually included in the cylinder marking or on a cylinder label. Each country may have their own specification, or they may accept the USA DOT specification. Within the USA, the government specification of an aluminum SCBA cylinder may be "DOT-3AL," for example, or "DOT-E9894". See FIGURES 1 - 4 for USA examples. See **labels** and **markings**.

A government's requirements for a composite cylinder are often written in an exemption. All Luxfer composite cylinders in the USA are regulated by exemptions which include information about the retest frequency and cylinder life. See **exemption**.

**heat effects on aluminum cylinders:** Metals (e.g., iron/steel and aluminum) change properties when exposed to high temperatures. Aluminum cylinders exposed to fire, arc welding, ovens, furnaces and other heat sources will become soft. Aluminum cylinders known to have been left unattended and exposed to heat sources over 350° F (175°C) are unsafe and must be condemned and removed from service. If you suspect an all-metal cylinder has been left unattended for a day or more, and heated to temperatures between 265°F (130°C) and 350°F (175°C) it must be hydrostatically retested before further use. At no time should any cylinder be heated (except for an occasional steam cleaning) in order to dry, cure or remove paint, or to dry a wet cylinder. See NOTE 20 and PHOTO 13 for important additional information.

**heavy service conditions:** Cylinders filled or topped off five or more times per week. Also, cylinders used wherever damage is more likely to occur than in normal use or where the care and/or maintenance is slightly below recommended care (see NOTE 4). Then cylinders must be inspected once a year or more frequently.

**hoop-wrapped:** As used in this Guide, it is meant to describe the composite cylinder design where the composite material is only put on the cylindrical portion of the container. The crown<sup>5</sup> and base of the liner are left as unwrapped aluminum. See **liner**.

**hydrostatic test:** A pressure test of the cylinder using a water jacket. The U.S. Department of Transportation (DOT) requires that this test (called a retest) be done on every all-aluminum cylinder every five years by a hydrostatic retester duly authorized by

the Research and Special Programs Administration. Similarly, under the exemption requirements for composite cylinders, the DOT specifies this retest be done on composite cylinders every three years. See NOTE 1 and APPENDIX F.

**hydrostatic retest date:** A date, consisting of the month and year, when a hydrostatic retest was performed after its manufacturer's hydrotest date. An all-aluminum cylinder will have retest dates for every five years or less after the manufacturer's first hydro test date. Exemptions specify how frequently a composite cylinder must be retested (usually every three years). See NOTE 1 and APPENDIX F.

**imperfection:** Used in this Guide, it means any visual fault or weakness in the cylinder (including thread, metal and composite areas). This includes, but isn't limited to: corrosion, damage (cuts, digs, gouges, scrapes, dents, etc.), cross threads, cracks, bulges, bow, folds, valleys, tool stop marks, loose fibers, missing resin, etc. Not all imperfections are material losses and may not pose a cylinder safety concern (e.g., tool stop marks). Each imperfection that does pose a cylinder safety concern is discussed in the Guide, which identifies acceptable limits that can be measured or estimated (e.g., pits), or condemnable features (e.g., a thread crack, fold, delamination, etc.).

**inspection:** See NOTE 22.

**isolated pit corrosion:** Pit corrosion, when the pit is alone or separated from other corrosion pits. See **pit corrosion**. See PHOTOS 11 and 12.

**labels:** Composite cylinders are not generally 'marked' (see **markings**) but are, instead, labeled. The exception may be hoop-wrapped cylinders, which may have retest information stamped into the crown portion. Composite cylinders have their information printed on labels that are then embedded in the composite material. Retest information for composite cylinders is most often put on labels and then those labels are put on the composite material of the cylinder and sealed with a coating of resin. However, hoop-wrapped cylinders may have retest markings stamped in the metal dome area. The resin-coated labels (and any stamped retest markings) must never be disturbed, removed or covered. If the serial number becomes illegible or is for any reason unknown, the SCBA cylinder must be condemned. If the first hydrotest date or manufacturer's or supplier's name, product identification, etc. on the original embedded label is obscured or at any time illegible, the cylinder must be taken out of service until the proper information is put back on the cylinder. See FIGURE 3 and 4.

**Level 1 damage:** A damage severity scheme put forth in CGA Pamphlet C-6.2 (see APPENDIX F). Level 1 damage includes that type of physical damage to composite materials which is minor and still makes the cylinder suitable for service.

**Level 2 damage:** A damage severity scheme put forth in CGA Pamphlet C-6.2 (see APPENDIX F). Level 2 damage includes the type of physical damage to composite materials which is allowed to be repaired by the application of a two-part, room temperature cure epoxy resin. Luxfer composites may be repaired if the damage (cuts, gouges, scratches, etc.) is over 0.005 inches (0.13 mm) deep, one inch (25.4 mm) or shorter in length, and is at or under the depths given in TABLE 1.

**Level 3 damage:** A damage severity scheme put forth in CGA Pamphlet C-6.2 (see APPENDIX F). Level 3 damage is physical damage to the composite portion of a cylinder which requires the cylinder to be condemned. Level 3 damage is any damage which exceeds Level 2 damage.

**line corrosion:** Pit corrosion occurring along a line in aluminum material. When pits are so close that they merge, or from a short distance appear to be a single corrosion along a narrow to broad line, the effect is called **line corrosion**. Cylinders left with water inside and then stored on their side often show interior line corrosion where the water's edge touches the cylinder wall. Line corrosion is sometimes seen where the cylinder boot, harness or straps may trap moisture against the aluminum exterior. Line corrosion is particularly detrimental to the safety of an aluminum cylinder. Follow condemning guidelines carefully. Proper care and maintenance will prevent line corrosion.

**liner:** The liner of a composite cylinder is very simply the material below the composite material. The metal portion of a hoop-wrapped container can be thought of as a liner. The liner is the form around which the composite material is wrapped around. Luxfer Gas Cylinders manufactures aluminum liners for many of its composite cylinders.

**markings:** The words, letters, numbers and symbols stamped into the aluminum portion of a cylinder. Manufacturing markings include cylinder information (date manufactured, date first hydro tested, cylinder type, service pressure [in psig or bar or both], serial number, manufacturer (Luxfer), etc.). Other markings include the hydrostatic retest date(s) and markings authorized to be added by the DOT. Composite hoop-wrapped cylinders may have retest markings stamped into the metal dome portion. See FIGURES 1 and 2.

In composite cylinders, the manufacturing information appears on the label embedded in the composite material. See **labels** above.

**material loss:** The removal of aluminum metal by corrosion or from physical abuse. The loss of material (aluminum) from any part of the cylinder is one of the most important concerns of cylinder safety. One of the reasons for regular and timely visual inspections, as well as inspections following a known condition (see under FREQUENCY in Section 1D) is to condemn cylinders which suffer unacceptable material loss. Material loss can also occur when owners (with good intention) try to sand a cylinder, or blast it with material to make it shiny or to restore a luster to the aluminum cylinder surface. These activities are not recommended, as surface treatments may result in sufficient material loss to cause leaks and ruptures. See PHOTO 2.

Material loss in a composite cylinder can be the removal of resin, delamination, or any removal of the wrapping fibers. Such 'loss' is generally considered a weakening of the composite portion of the cylinder and may lead to leaks or ruptures. See PHOTO 25.

**metal alloys:** Over the years, different metal mixtures have been used to manufacture SCBA cylinders. These metal mixtures are called alloys. Different alloys of steel and aluminum have been used by many different manufacturers. Generally, when one considers an 'aluminum alloy' the majority of the metal mixture is aluminum. See **aluminum alloys**.

**metal distortions:** During the manufacturing process, some aluminum metal may not flow smoothly, causing sections or areas to form ridges, valleys, folds, and misshaped deviations from the normal smooth and uniform metal. These manufacturing imperfections may generally be termed **metal distortions**. See PHOTOS 3, 14, 15, 16 and 17. See **fold, imperfection, and valley**.

**NDT:** Non-destructive test(ing). A particularly useful means for quickly and accurately determining whether or not there are thread cracks present—even the ones that are very hard to see.

**neck:** The top portion of the crown, containing the threads, face and O-ring gland. See FIGURE 6.

**neck ring:** Luxfer DOT E 7235 cylinders with a 4500 psig service pressure require the use of a steel ring around the threaded neck. This 'neck ring' reinforces and strengthens the threaded area of this cylinder design and is required. Cylinders of this design were 'retrofitted' with a neck ring. Cylinders of this design must not be used unless they have a neck ring. Contact Luxfer (see NOTE 7) if you have such a cylinder without a neck ring.

**normal service:** An SCBA cylinder in normal service under 'average' SCBA service conditions is well cared for, handled, and maintained according to guidelines in NOTE 4. These cylinders are not subject to frequent use (more than two fills per week), nor are they subject to conditions likely to damage them (e.g., working in tight spaces where damage to the cylinder is likely to occur). If in normal service, all-aluminum cylinders covered by this Guide should be inspected every thirty months or less. Hoop-wrapped composite cylinders covered by this Guide should be inspected every 18 months or less.

**O-ring:** The gasket placed between the cylinder neck and the valve, forming an air-tight seal. Each valve manufacturer specifies the kind of O-ring to use with the valve as well as its proper installation. Some manufacturers will recommend that the O-ring be replaced whenever the valve is removed. Be sure to follow the valve manufacturer's suggested procedures for O-ring replacement and installation.

**O-ring gland:** The top portion of the cylinder in the neck which is cut into the aluminum to fit the O-ring. Also referred to as a "seat." Usually a depression in the metal just below the face into which the O-ring fits. The installation of the valve squeezes the O-ring to press against the bottom and side of the gland to make an air tight seal. If the O-ring gland is damaged (gouge, cut, scrape, etc.) it may cause an air leak. See FIGURE 6.

**Organization:** The entity that provides the direct management and supervision for emergency incident response personnel. Examples of such entities include, but are not limited to, fire departments, police departments, rescue squads, EMS providers, HAZMAT response teams and entities (such as hazardous material manufacturing facilities, facilities with confined spaces, etc.) who keep and use SCBAs for private response teams.

**pit:** A hole or cavity in the metal or composite material of a cylinder. Usually caused by corrosion (metal), chemicals, or a sharp object. The pit may or may not be 'straight.' Other possibilities include the many types of corrosion paths outlined in this procedure and the kinds of metal pit formations shown in FIGURE 9. Since not all corrosion pits are identical in shape, the inspector should take a few moments to inspect or probe the pit to get an idea of its overall shape and profile before estimating its depth.

**pit corrosion:** Corrosion which makes a pit. Pit corrosion is particularly detrimental to the safety of an aluminum cylinder. Its depth and shape should be the primary concern of a good inspection, since pits beyond certain depths may render the cylinder unsafe. See PHOTOS 11 and 12. See FIGURE 9. Proper care and maintenance prevents pit corrosion.

**psig:** An acronym pressure parameter for a gas, standing for pounds per square inch gauge of a gas. Some use "psi" which is "pounds per square inch" but in this Guide, since all references are to gauge pressures, the more specific and accurate acronym, "psig" is used. Sometimes written "p.s.i.g.," the 'gauge' portion references the standard pressure above the atmospheric pressure of 14.7 psi.

**repair:** Under certain conditions, the composite portion of the composite SCBA may be repaired. The procedure is given in NOTE 13. After the repair is complete, the cylinder must be hydrostatically tested before being put back into service. The retester operating in the USA and those retesters following DOT requirements must be notified that the cylinder they are getting has been repaired. Repaired cylinders must pass a specific retest visual inspection special to them, in accordance with CGA Pamphlet C-6.2 (see APPENDIX F).

**RSPA:** Research and Special Programs Administration agency within the USA DOT. For their function related to SCBA cylinders, see NOTE 1.

**respiratory equipment:** Used in this Guide to refer to the equipment making up the basic SCBA. Similar to the definition of 'respiratory system' below, but not thought of as a "certified set" of equipment.

**respiratory system:** Used in this Guide to refer to the Luxfer SCBA cylinder and all the other attachments and components to the respiratory equipment which is provided by a respiratory manufacturer as a 'certified set.' The system is usually certified and approved by a regulatory agency (in the USA) and its components cannot be changed or replaced with parts not conforming to the system's certification. The parts are compulsory in the sense that each part of the system is certified as a part of the SCBA. Respiratory system (SCBA) manufacturers must be contacted to find out what part is approved to act as replacement parts to their certified system.

**retrofit:** The Luxfer DOT E 7235 cylinder with a 4500 psig service pressure was originally sold without a neck ring. Later, it was determined that the cylinder design required the fitting of a neck ring around the outside of the threaded neck area. These cylinders were fitted with a steel neck ring (see **neck ring**). The fitting is called 'retrofit.' Cylinders that have been correctly retrofitted have a black and white sticker on the crown that says, "Retrofitted." Through service, following the retrofit, some retrofitted cylinders could exist without a sticker and should not be removed from service because of this.

**SCBA:** Used in this Guide to mean the respiratory apparatus known as the self-contained breathing apparatus. The 'apparatus' is a combination of equipment and components which may or may not be certified and regulated in the country, state, province, or place of use. When the SCBA is certified, then each component is specified for use in that respiratory system (SCBA system). In this Guide, unless otherwise specified, it is assumed that "SCBA" means a certified set of respiratory equipment and components, which makes a complete system for breathing air from a high pressure cylinder.

**SCBA cylinder:** SCBA cylinders manufactured by Luxfer Gas Cylinders to hold breathable air at pressures of 2216 psig or more.

**scrape:** To rub with something rough or sharp causing a scuff abrasion and/or scratches. The Super Scraper by Motsenbocker, when used properly, slides along the aluminum surface of the cylinder without causing any scrape damage to the cylinder surface (see APPENDICES B and C).

**shoulder:** The top part of the cylinder from the sidewall to the neck. Most of the crown portion, except for the threaded area. See FIGURE 5.

**shoulder cracks:** Splits or fractures in the metal, in the top part of the cylinder. See PHOTO 20.

**sidewall:** The straight smooth portion of a SCBA cylinder between the base and the crown. The metal thickness is uniform in this region.

**stamped markings:** See **markings**. For examples of Luxfer stamped markings used over the years, see FIGURES 1 - 4.

**stripped thread:** Threads which have been removed, or torn.

**structural damage:** Generally used to describe severe damage to composite containers. Such damage may involve damage to the liner, sometimes only visible by doing an internal inspection. Any composite container showing external indentations or that may have been crushed or squeezed has suffered structural damage. If the composite cylinder does not roll smoothly on the table top during the inspection test for dents and bows, then the cylinder must be carefully inspected to determine if there has been structural damage. Condemn all containers with structural damage or with suspected structural damage.

**tap:** A tool to machine threads into a metal. See **tool stop mark**.

**thread:** The top portion of the cylinder, in the neck, which contains a fine helical filament of metal which meshes with the same of a valve. See FIGURE 5, PHOTOS 4 - 10 and 19.

**thread cracks:** A split or fracture in the threaded portion of the cylinder. It is usually jagged. See PHOTOS 6 - 9. Not to be mistaken for a "tool stop mark."

**thread gall:** Imperfections in the threaded area caused by many possible physical abuses. Thread gall is usually caused when inappropriate (wrong size valves or wrong threaded valves), unclean, deformed, or damaged threaded items (e.g., valves) are forced (screwed) into the cylinder thread. When debris in the cylinder thread or debris on the valve thread is ground into the cylinder thread, such as when the valve is installed, gall will often occur. Threads too large, improperly sized, damaged or deformed, if forced into a cylinder's thread may cause gall, if not ruining the cylinder's thread. See **gall** and **cross threads**.

**tool stop mark:** When the tool (tap) is stopped, after machining threads in metal, there is occasionally a faint, shadowy line left on the thread. Sometimes called a "tool mark" or "tap stop". The line is straight, passing down through most of the entire thread area. The tool stop mark doesn't affect the quality, safety or performance of the cylinder or thread area. Without accurate and careful inspection, the tool stop may appear to be a crack. The visual inspector must learn the difference between a tool stop mark (something which doesn't affect the safety or quality of the cylinder) and a crack (something which may cause the cylinder to leak or rupture). See PHOTO 10.

**torque wrench:** A conventional-type wrench which will 'click' (make an audible sound) or 'slip' when too much force is applied to it. The desired setting on the wrench is made prior to its use. The recommended equipment for use when reinstalling cylinder valving.

**transverse:** A direction near right angles from the direction of the fiber wrapping. Fibers are wrapped on the aluminum in a direction that can be determined by looking closely at an area of the composite material. A 'transverse' direction to the fiber wrapping will be in a direction that 'cuts' across the path of the fiber wrap. When a scratch, cut, gouge, etc. is in a transverse direction, it may cut fibers if long and/or deep enough.

**upset metal:** Metal which has been pushed or moved to rise above the regular surface of the metal around it. When aluminum is gouged, scraped, etc. some of the metal, at the edge of the damage, may be raised or set higher than the unaffected metal in the vicinity. In general, the raised or upset metal may be filed and smoothed to the regular surface, so an accurate depth measurement of the imperfection can be taken. Care must be taken so as to not remove metal which is part of the wall thickness in the original design of the cylinder. See **material loss**.

**valley:** The place between two metal flows which meet in such a manner as to create a shallow and smooth elongated depression. The valley will always be along the length of the cylinder and usually in the crown area. See FIGURE 7 and PHOTOS 16 and 17. Compare this to **fold**.

**valve:** The control device installed into the threaded opening of a cylinder to restrain and manage the compressed air. Various manufacturers make valves and accessories for SCBA cylinders. Brass and/or copper alloy valves should not be used in aluminum cylinders unless they have been thoroughly and properly plated with chrome or nickel so that the brass and/or copper doesn't come into contact with the aluminum. See **corrosion** and **galvanic corrosion**.

**visual inspection procedure:** A procedure primarily relying upon the sense of sight to examine, investigate and observe the condition of a cylinder. See **inspection**.



# FIGURES

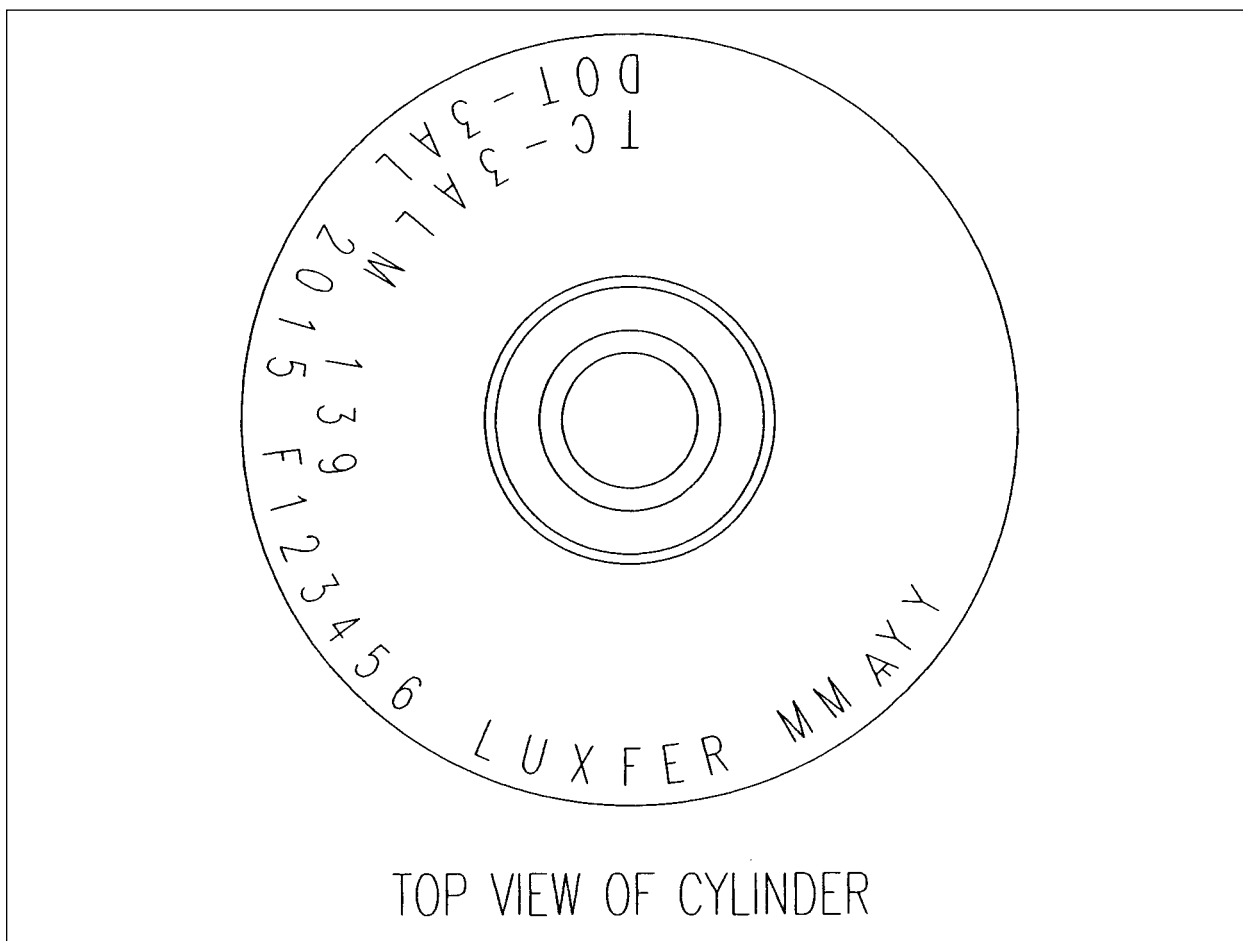


FIGURE 1.

### Interpretation

#### Bottom Row

01. U.S.A. Governmental Specification:
02. Service Pressure (p.s.i.g.):
03. Serial Number:
04. Manufacturer:
05. Original Hydro Date with Testing Agency Stamp:

### Marking Example

DOT-3AL  
2015  
F123456  
LUXFER  
MM YY

#### Top Row

01. Canadian Governmental Specification:
02. Service Pressure (bar):

TC-3ALM  
139



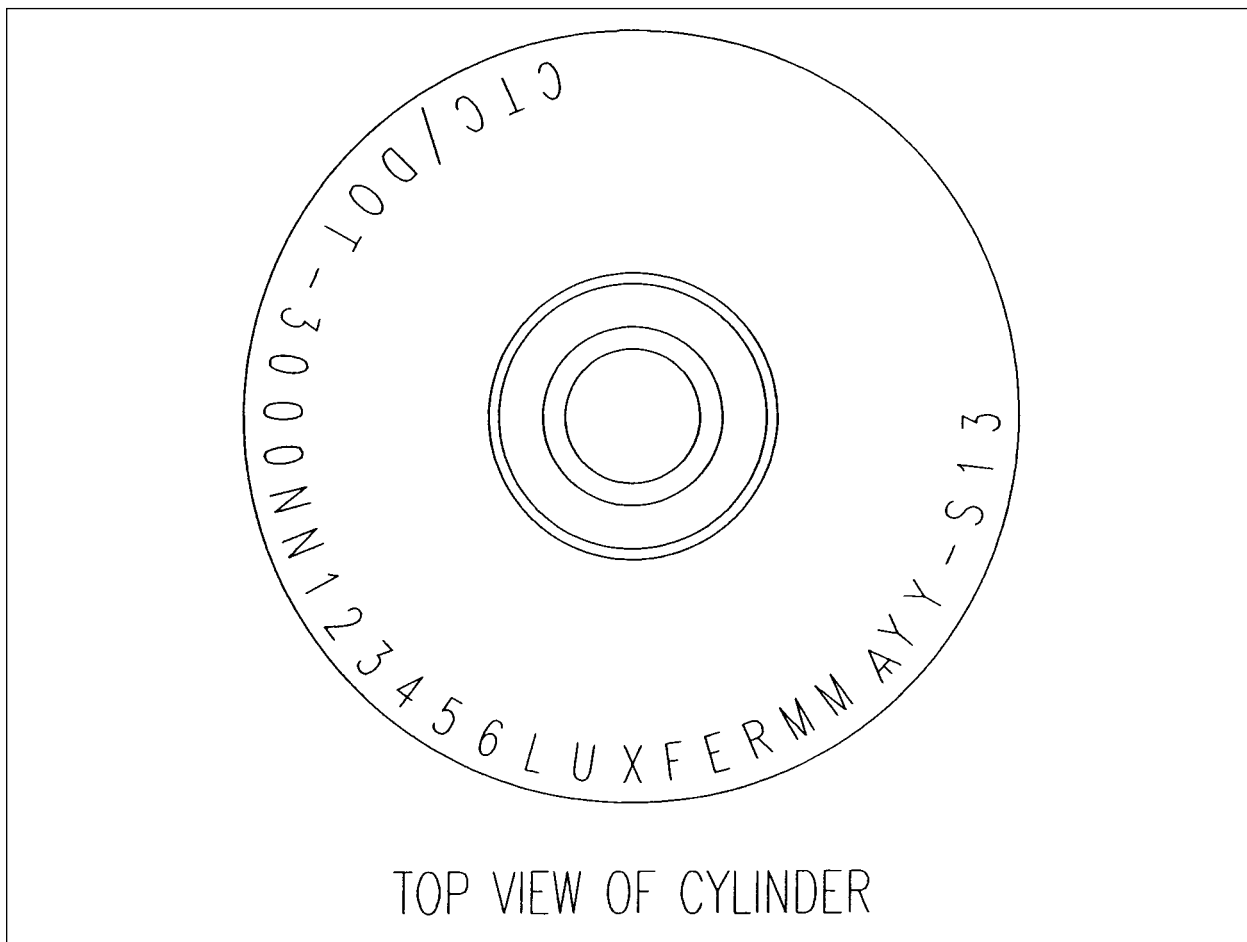


FIGURE 2.

**Interpretation**

**Marking Examples**

**Bottom Row**

- |   |             |
|---|-------------|
| 01. U.S.A. and Canadian Governmental Specification: | CTC/DOT-3AL |
| 02. Service Pressure (p.s.i.g.):                    | 3000        |
| 03. Serial Number:                                  | NN123456    |
| 04. Manufacturer:                                   | LUXFER      |
| 05. Original Hydro Date with Testing Agency Stamp:  | MM YY       |
| 06. Luxfer U.S.A. SCUBA cylinder type:              | -S13        |

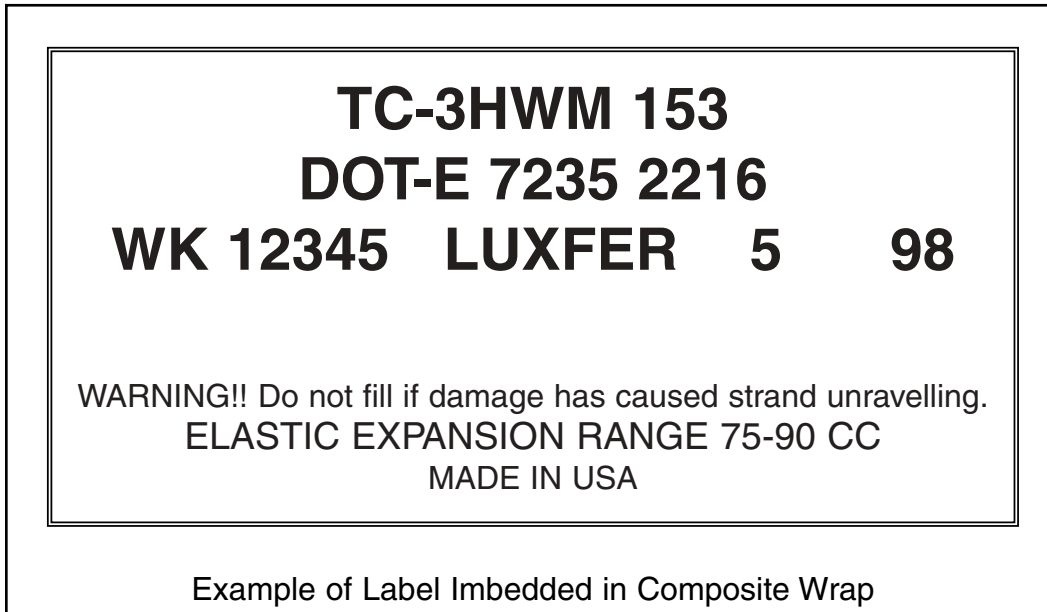


FIGURE 3.

**Marking Requirements**

Canadian Governmental Specification  
Service Pressure (bar)  
DOT Exemption Number  
Service Pressure (psi)  
Serial Number  
Manufacturer  
Original Hydro Date with Testing Agency stamp

**Example**

TC-3HWM  
153  
DOT-E 7235  
2216  
EK 12345  
LUXFER  
MM YY

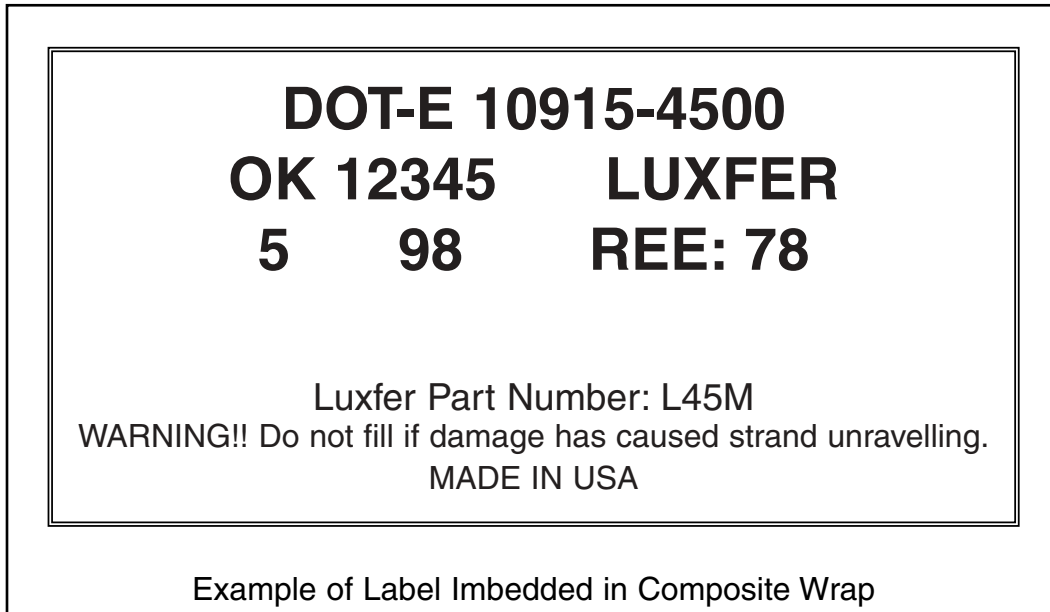


FIGURE 4.

**Marking Requirements**

DOT Exemption Number  
 Service Pressure (psi)  
 Serial Number  
 Manufacturer  
 Original Hydro Date with Testing Agency Stamp  
 Rejection Elastic Expansion (cc)

**Example**

DOT-E 10915  
 4500  
 OK 12345  
 LUXFER  
 MM YY  
 REE: 78

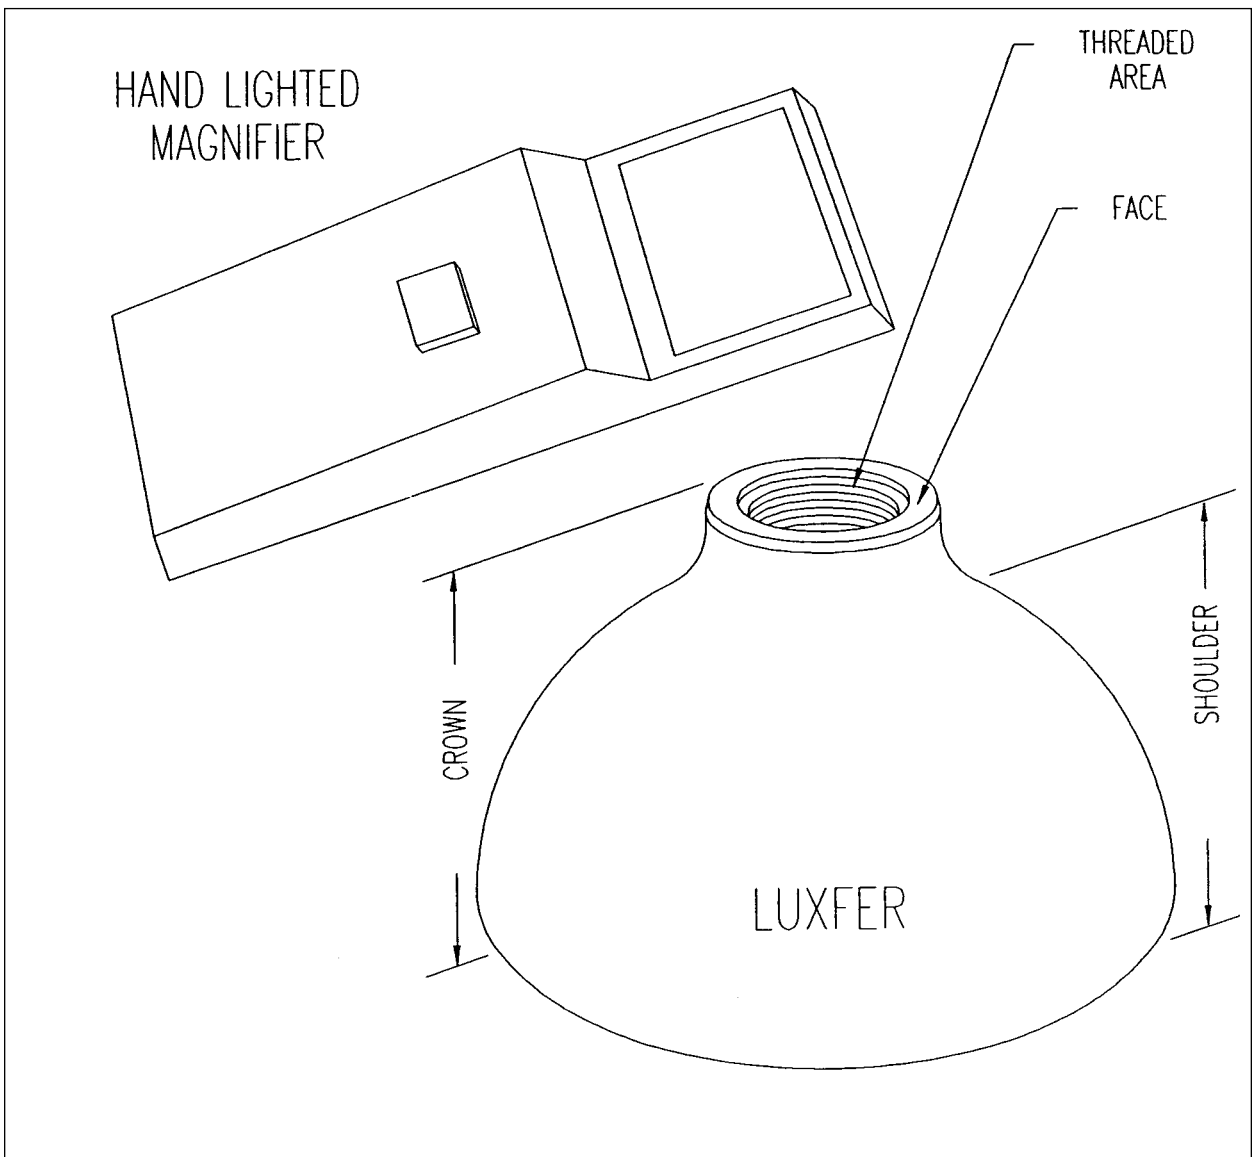
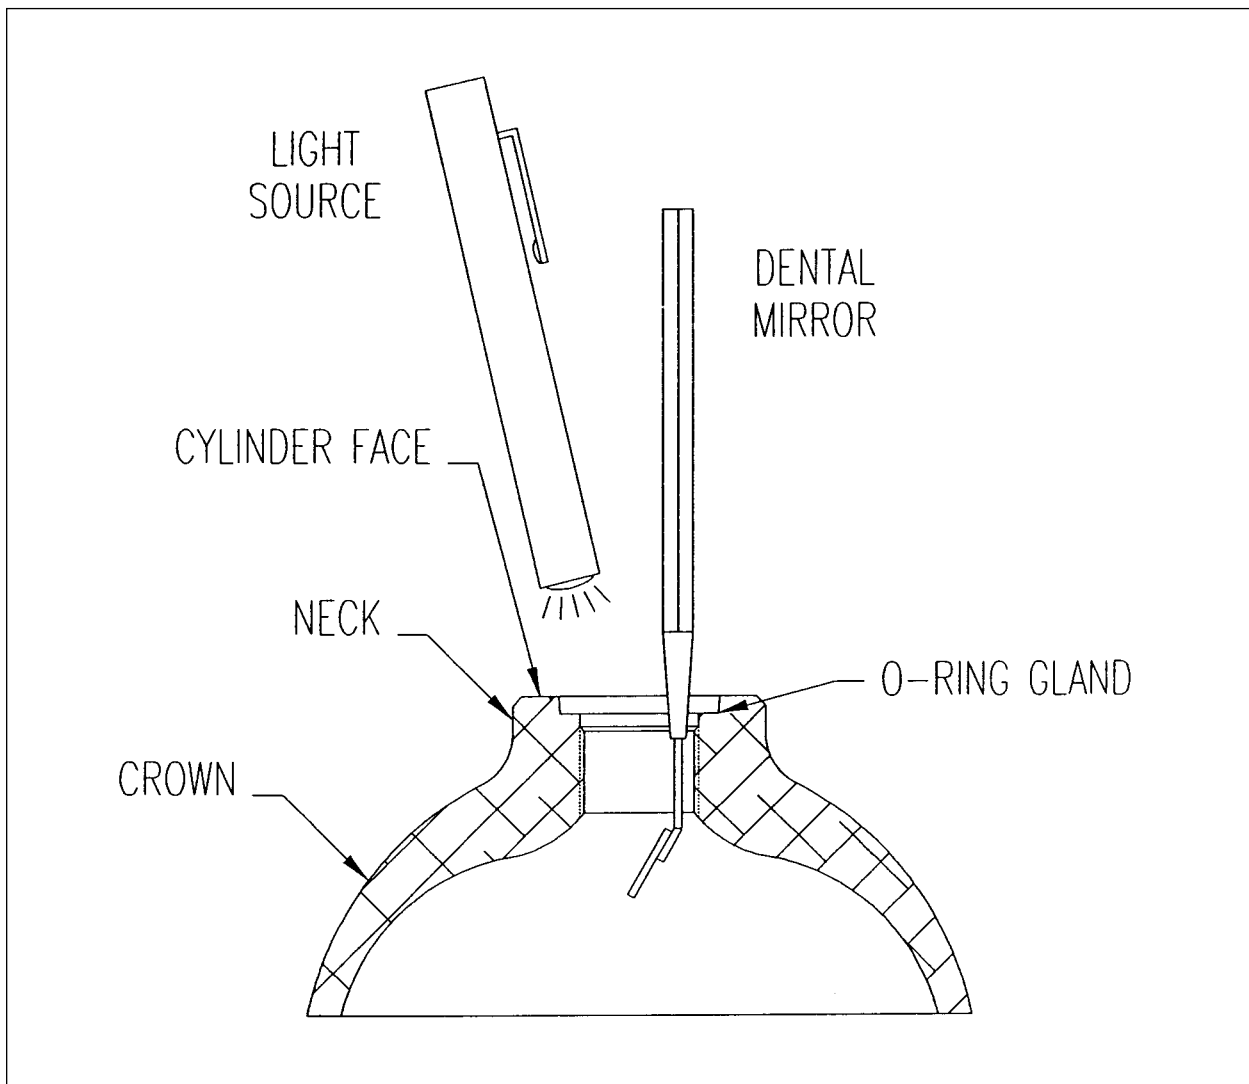


FIGURE 5.

FIGURE 5 shows a MAGNA-LITE Model #1502, 3 power wide-angle, hand-lighted magnifier and a Luxfer USA Limited crown section.



**FIGURE 6.**

Dental mirror in position with a light source to adequately illuminate the interior of the crown area of the cylinder which allows the user to perform a successful inspection. See PHOTO 20.

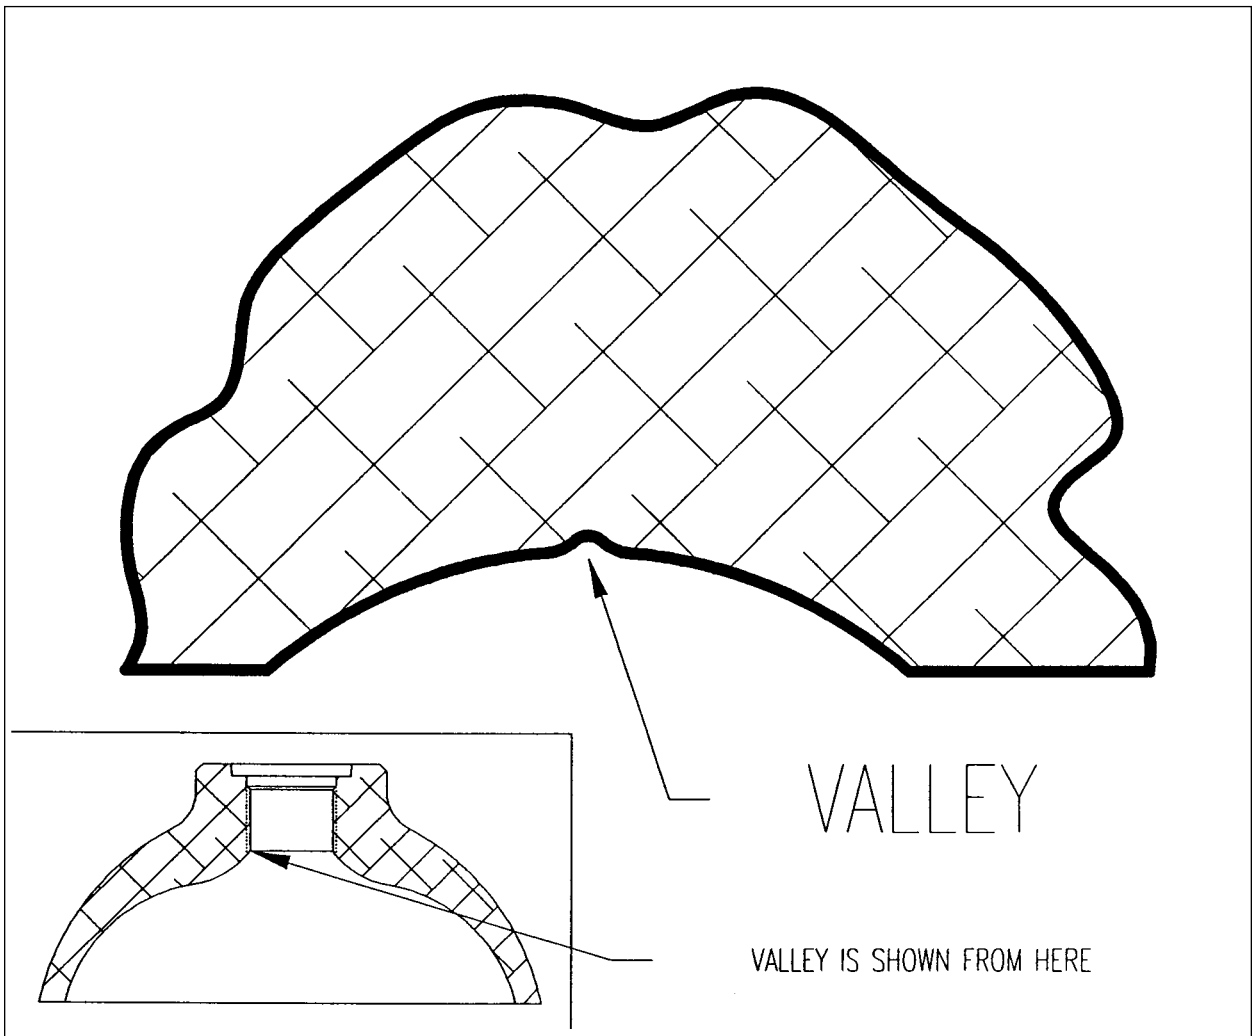


FIGURE 7.

In FIGURE 7, the valley is shown from a cross sectional view of the bottom of the threaded area. The valley has a rounded effect in the metal flow. See PHOTO 16 and 17.

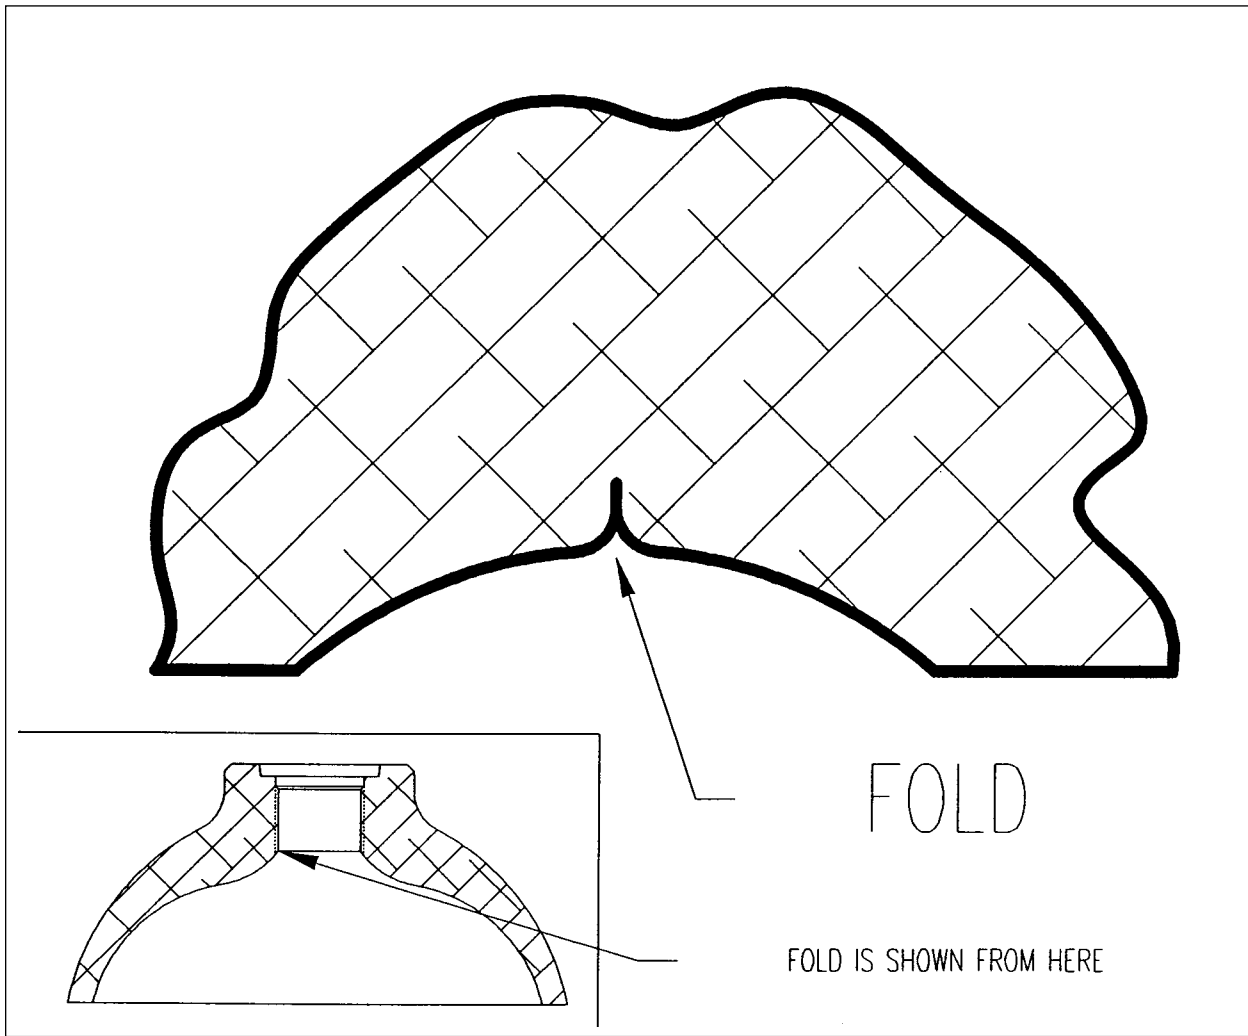


FIGURE 8.

In FIGURE 8, the fold is shown from a cross sectional view of the bottom of the threaded area. The fold has a definite flow back into the shoulder. See PHOTO 14 and 15.

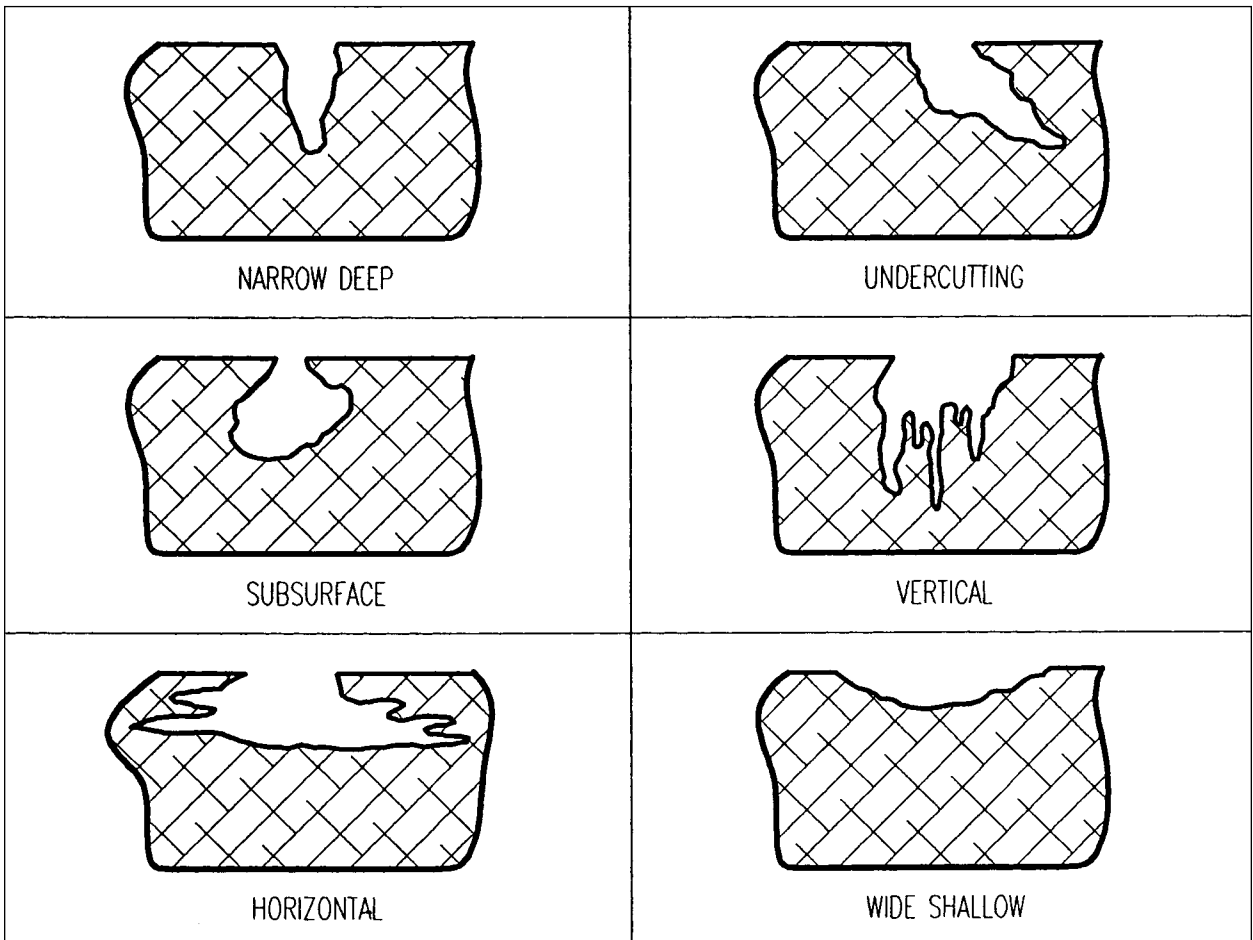
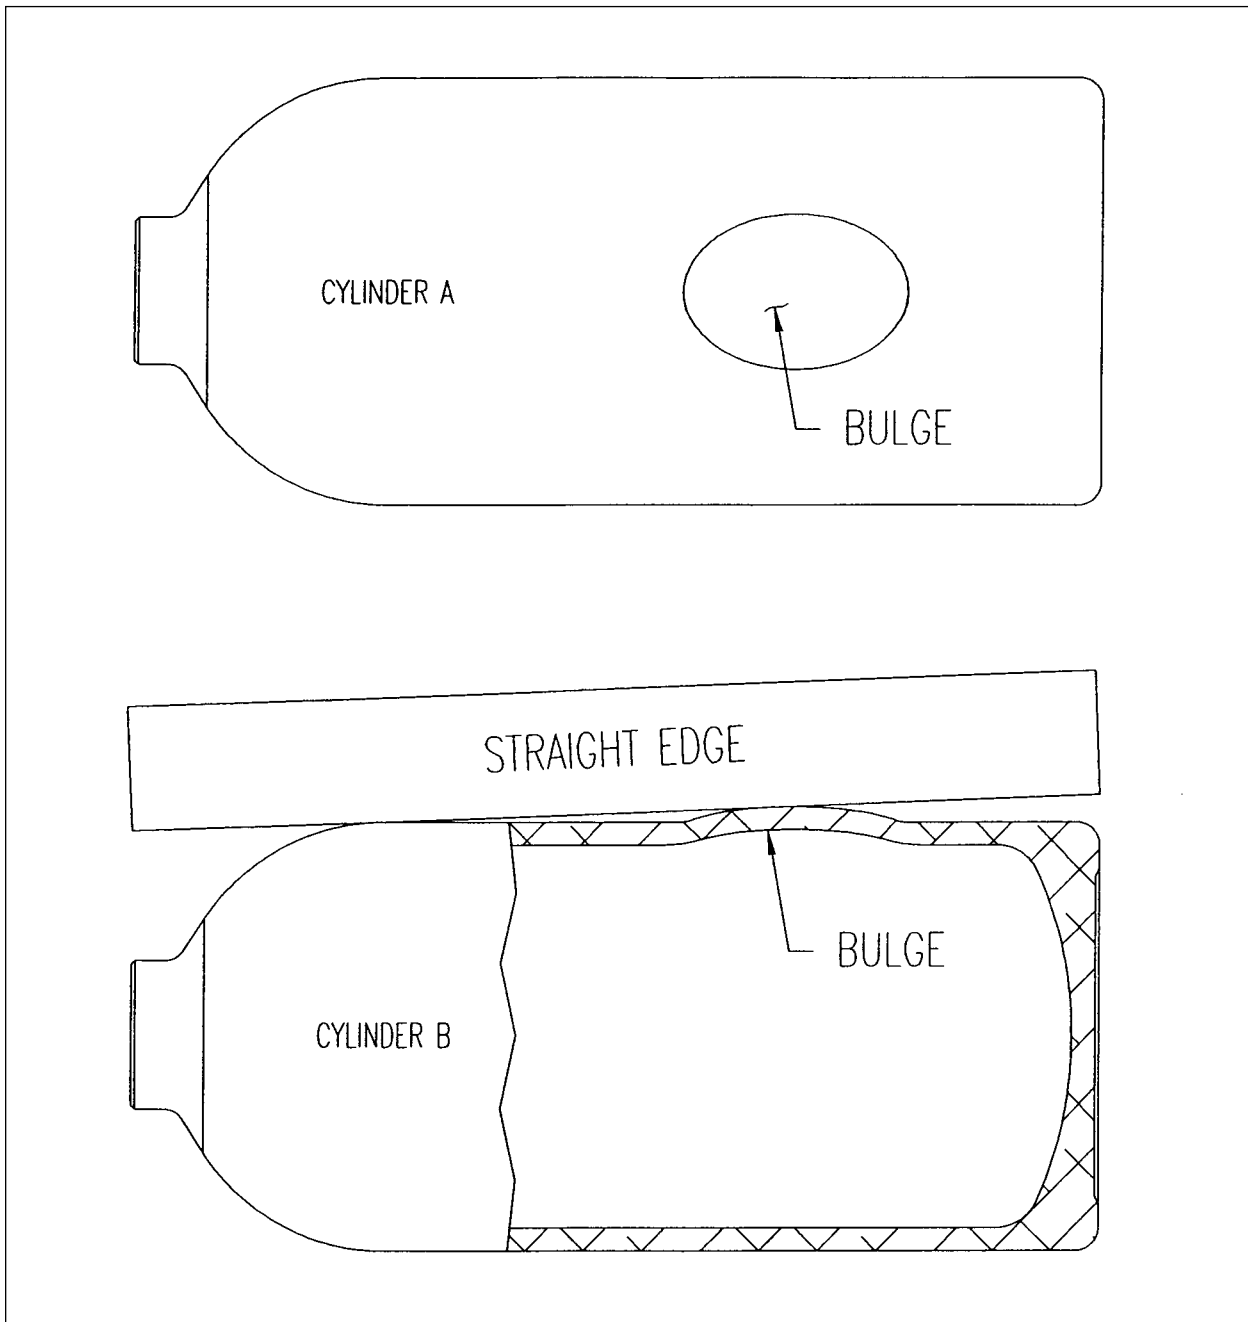


FIGURE 9.

In FIGURE 9, the various shapes of pits are shown from a cross sectional view of the sidewall, base or crown section of the cylinder. The gap section of the pits represents where the sidewall, base or crown metal was, before pitting began. All cross sections are greatly magnified.





**FIGURE 10.**

Cylinder (A) shows the bulge externally and cylinder (B) is a cutaway of cylinder (A) and shows the same bulge internally. To find a bulge use any straight edge along the sidewall of the cylinder. Any cylinder with a bulge is to be condemned.

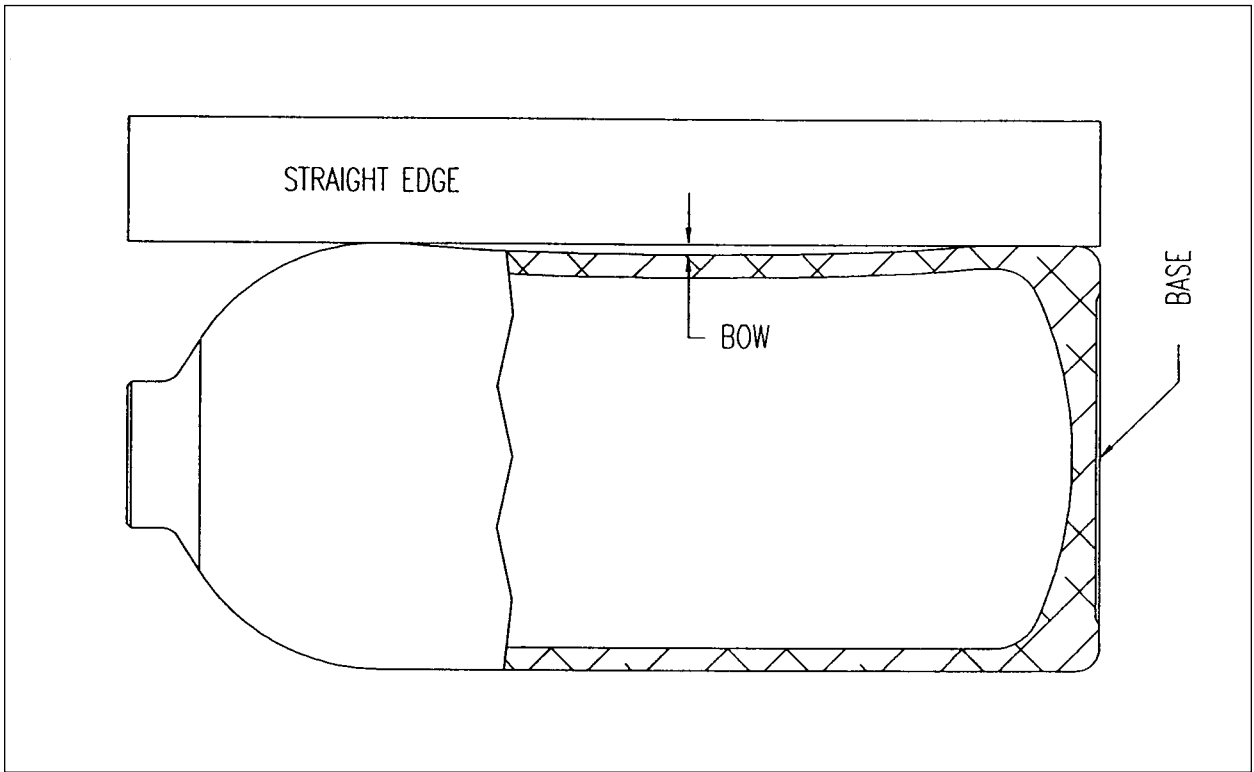


FIGURE 11.

To find a bow, lay the cylinder on its side. With any straight edge set at the base and on the spherical radius crown section, find the greatest gap between the straight edge and the sidewall of the cylinder.